

Disordered Materials:

Lecture II

*Finding and refining a structural
model*

Alan Soper

Disordered Materials Group

ISIS


Summary of Lecture I

- Discussion of disorder in our world.
- Concept of correlation in disordered systems.
- Use of radial distribution function to characterise the correlations in a disordered system.
- Use of diffraction to count atoms as a function of distance.
- How to characterise structure in molecular systems:
 - SDF, bond angle distributions, OPCF

Summary of lecture II

- Extracting the structure factor from the diffraction experiment.
- Computer simulation as a tool to model disordered materials
- Use of computer simulation to go from measurements ($D(Q)$, $g(r)$) to SDF, bond angle distribution, OPCF, etc.
- Some case studies: molten alumina, water, amorphous phosphorus, silica, silicon...

ISIS SANDALS (liquids diffractometer)

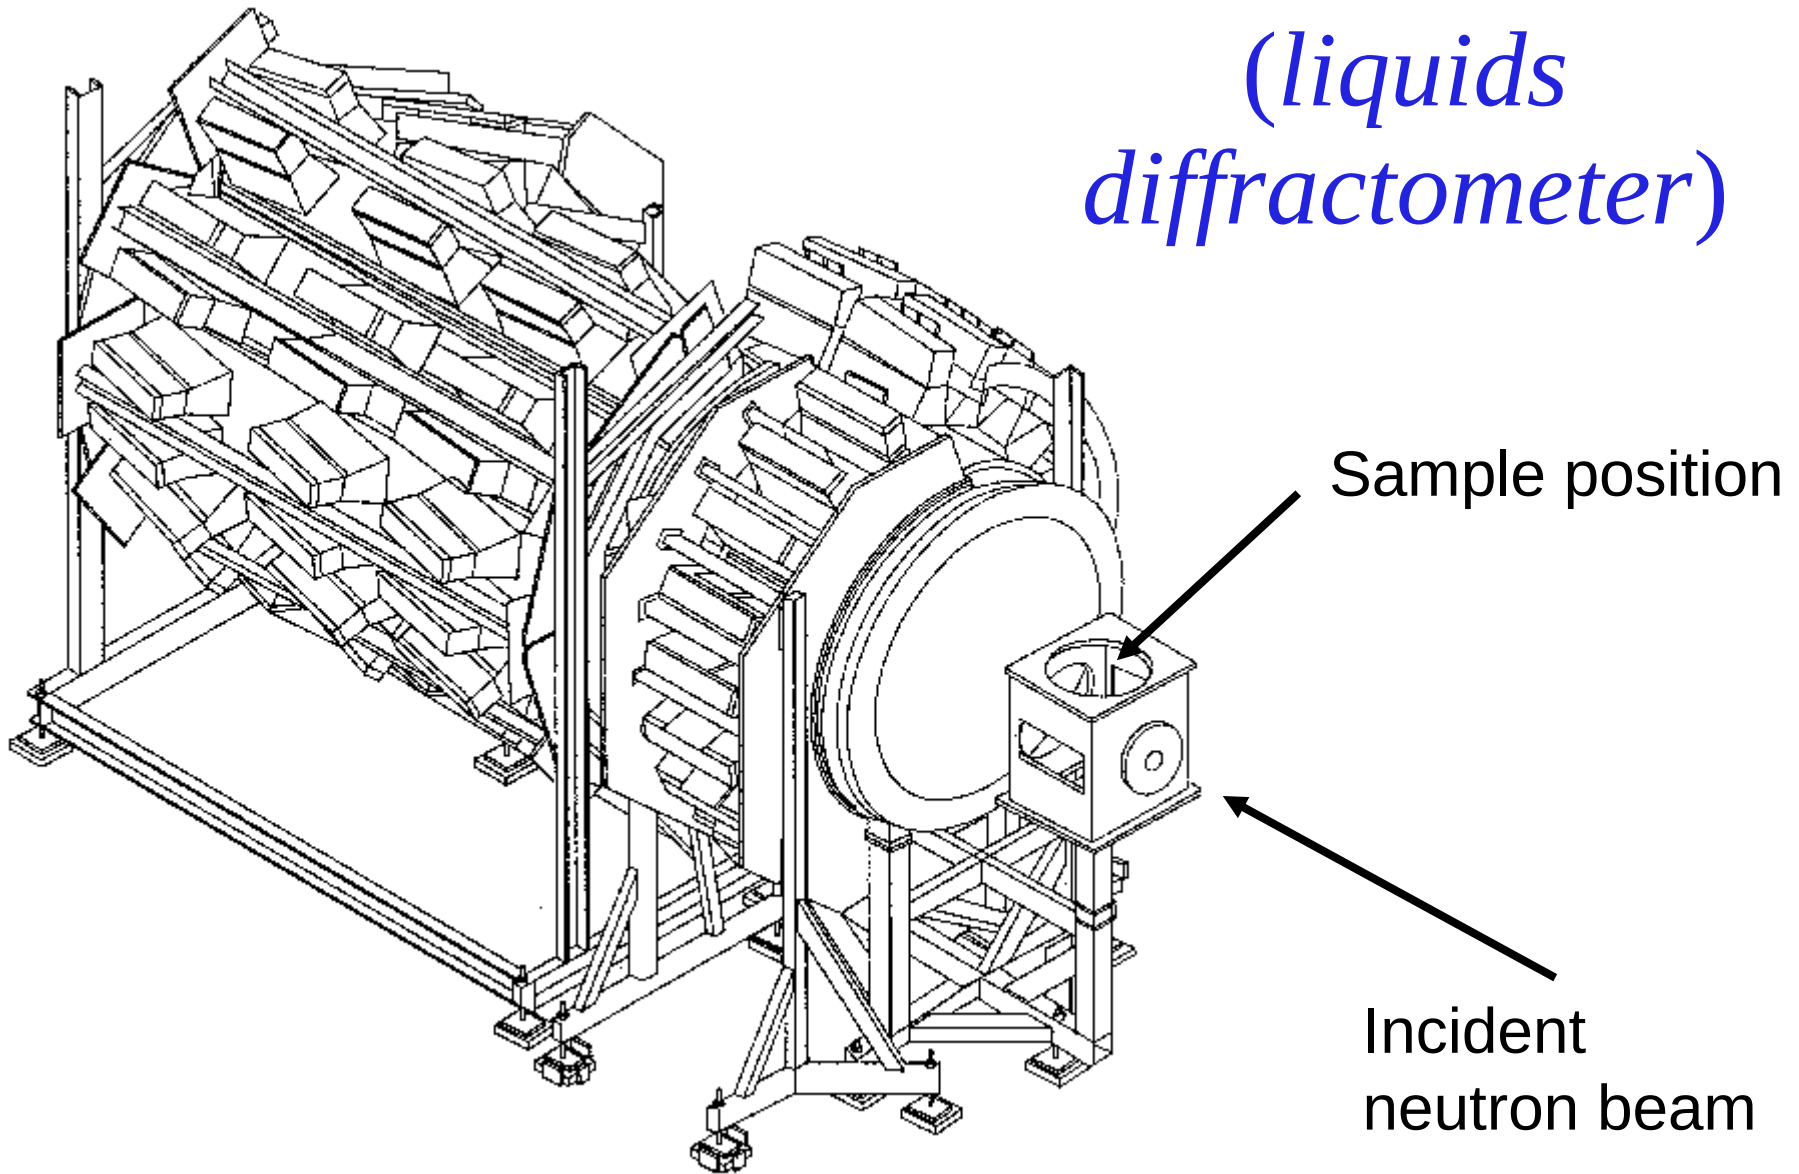

The liquid structure factor:

The partial structure factors, $H_{\alpha\beta}(Q)$

The site-site radial distribution functions, $g_{\alpha\beta}(r)$

$$F_d(Q) = \sum_{\alpha, \beta \geq \alpha} (2 - \delta_{\alpha\beta}) c_\alpha c_\beta b_\alpha b_\beta \left\{ 4\pi\rho \int r^2 (g_{\alpha\beta}(r) - 1) \frac{\sin Qr}{Qr} dr \right\}$$

Atomic fraction of component “ α ”

The atom scattering factor or “form factor”

*A much more tricky question:
how do we interpret the data?*

- For many years the next step was to simply invert our scattering equation:

$$\begin{aligned}
 d(r) &= \frac{1}{2\pi^2\rho} \int_0^\infty Q^2 D(Q) \frac{\sin Qr}{Qr} dQ \\
 &= \sum_{\alpha, \beta \geq \alpha} \left(2 - \delta_{\alpha\beta}\right) c_\alpha c_\beta b_\alpha b_\beta \left(g_{\alpha\beta}(r) - 1\right)
 \end{aligned}$$


This leads to many problems

- Truncation errors.
- Systematic errors.
- Finite measuring statistics.
- Some site-site terms are more strongly weighted than others.
- These all make interpretation of the data unreliable.
- Radial distribution functions ($g(r)$) do not yield the Orientational Pair Correlation Function (OPCF).

Introduce: computer simulation

- Requires an atom-atom potential energy function.
- Place computer atoms in a (parallelepiped) box at same density as experiment.
- Apply periodic boundary conditions
 - the box repeats itself indefinitely throughout space.
- Apply minimum image convention.

Minimum image convention

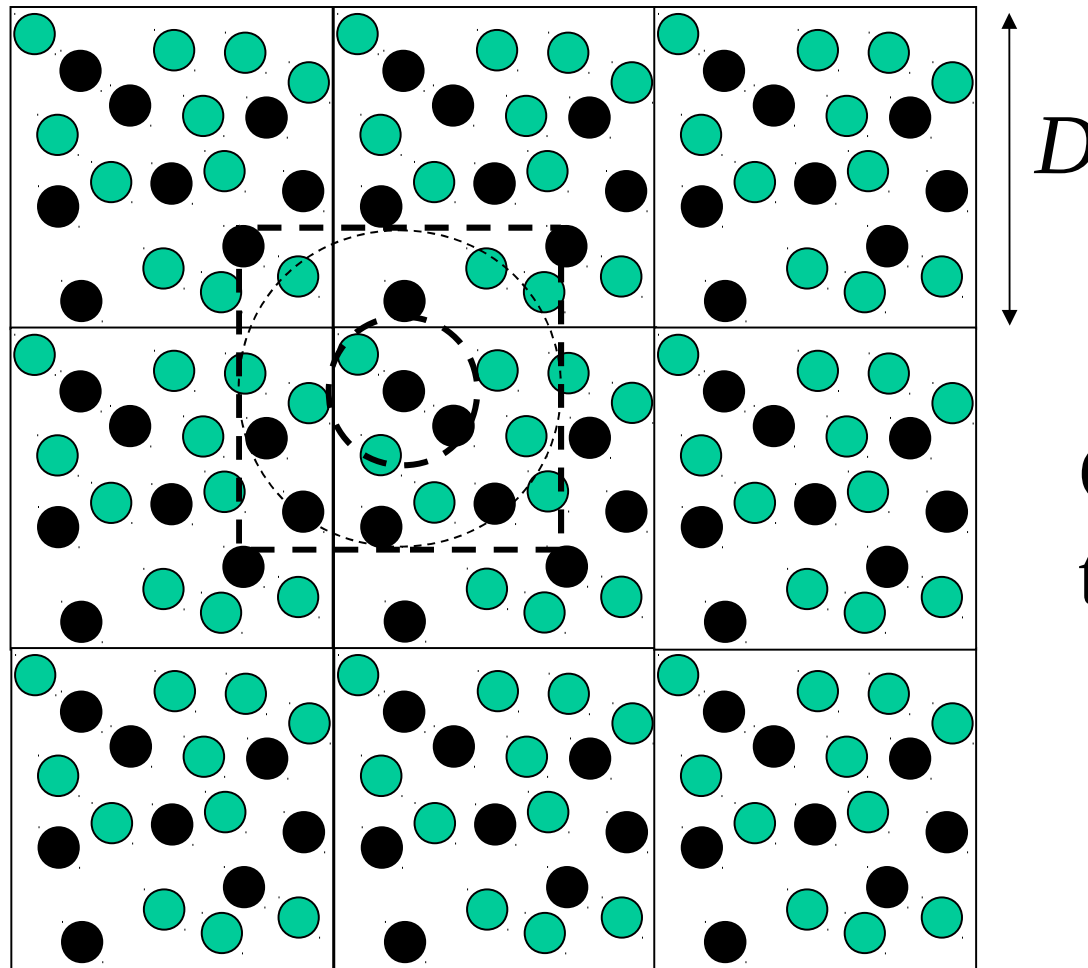

Count atoms out
to $D/2$

Monte Carlo computer simulation

1. Using the specified atom-atom potential function, calculate energy of atomic ensemble.
2. Displace one atom or molecule by a random amount in the interval $\pm\delta$.
3. Calculate change in energy of ensemble, ΔU .
4. Always accept move if $\Delta U < 0$
5. If $\Delta U > 0$, accept move with probability $\exp[-\Delta U/kT]$.
6. Go back to 2 and repeat sequence.

But there is a problem:

We don't know the potential energy
function!

Introduce Reverse Monte Carlo, RMC

1. Build a box of atoms as before. Calculate $\chi^2 = [D(Q) - F(Q)]^2 / \sigma^2$
2. Displace one atom or molecule by a random amount in the interval $\pm\delta$.
3. Calculate change in χ^2 of ensemble, $\Delta\chi^2$.
4. Always accept move if $\Delta\chi^2 < 0$
5. If $\Delta\chi^2 > 0$, accept move with probability $\exp[-\Delta\chi^2]$.
6. Go back to 2 and repeat sequence.

*This approach has problems,
particularly with molecules.*

- Molecules are usually introduced via unphysical coordination constraints.
- Especially with molecules the ensemble of atoms can get “stuck” i.e. it does not sample phase space correctly.
- Various reasons why this can occur.

Introduce Empirical Potential Structure Refinement, EPSR

- Use harmonic constraints to define molecules.
- Use an existing “reference” potential for the material in question taken from the literature (or generate your own if one does not exist).
- Use the diffraction data to perturb this reference potential, so that the simulated structure factor looks like the measured data.

Introducing the data

$$F(Q) = \sum_{\alpha, \beta \geq \alpha} \left(2 - \delta_{\alpha\beta} \right) c_{\alpha} c_{\beta} b_{\alpha} b_{\beta} H_{\alpha\beta}(Q)$$

- M measured datasets, N partial structure factors: (Usually $M < N$)
- Assign a “feedback” factor f for the data:

$$w'_{ij} = f w_{ij}, \quad 1 \leq i \leq M$$

- and $(1 - f)$ for the simulation:

$$w'_{ij} = (1 - f) \delta_{(i-M),j}, \quad M < i \leq M+N$$

- Form inversion of $w'_{ij}, \quad 1 \leq i \leq M+N, \quad 1 \leq j \leq N$

Refining the potential: M datasets, N partial structure factors


$$F_{i(=1, M+N)}(Q) = \begin{matrix} \text{Data} \\ \left[\begin{array}{cccccc} fw_{11} & fw_{12} & \dots & & \dots & fw_{1N} \\ fw_{21} & fw_{22} & \dots & & \dots & fw_{2N} \\ \dots & \dots & & & & \dots \\ \dots & \dots & & & & \dots \\ fw_{M1} & fw_{M2} & & & & fw_{MN} \\ (1-f) & 0.0 & 0.0 & \dots & \dots & 0.0 \\ 0.0 & (1-f) & 0.0 & \dots & \dots & \dots \\ 0.0 & 0.0 & (1-f) & \dots & & \\ \dots & \dots & \dots & \dots & & \end{array} \right] \\ \text{Simulation} \\ \left[\begin{array}{cccccc} & & & \dots & & \\ & & & & \dots & \\ & & & & & \dots \\ & & & & \dots & \dots \\ & & & & \dots & (1-f) & 0.0 & 0.0 \\ \dots & & & & \dots & 0.0 & (1-f) & 0.0 \\ \dots & \dots & & & \dots & 0.0 & 0.0 & (1-f) \\ 0.0 & \dots & \dots & & \dots & \dots & \dots & \end{array} \right] \end{matrix} \times \begin{matrix} \left[\begin{array}{c} S_1 \\ S_2 \\ \dots \\ S_N \end{array} \right] \end{matrix}$$

$$\Delta U_j(r) = \text{Fourier Transform of } \left\{ \sum_{i=1, M} w'_{ij}^{-1} (D_i(Q) - F_i(Q)) \right\}, \quad j=1, N$$


Structure refinement of liquid water

*Water
data*


*After
structure
refinement*

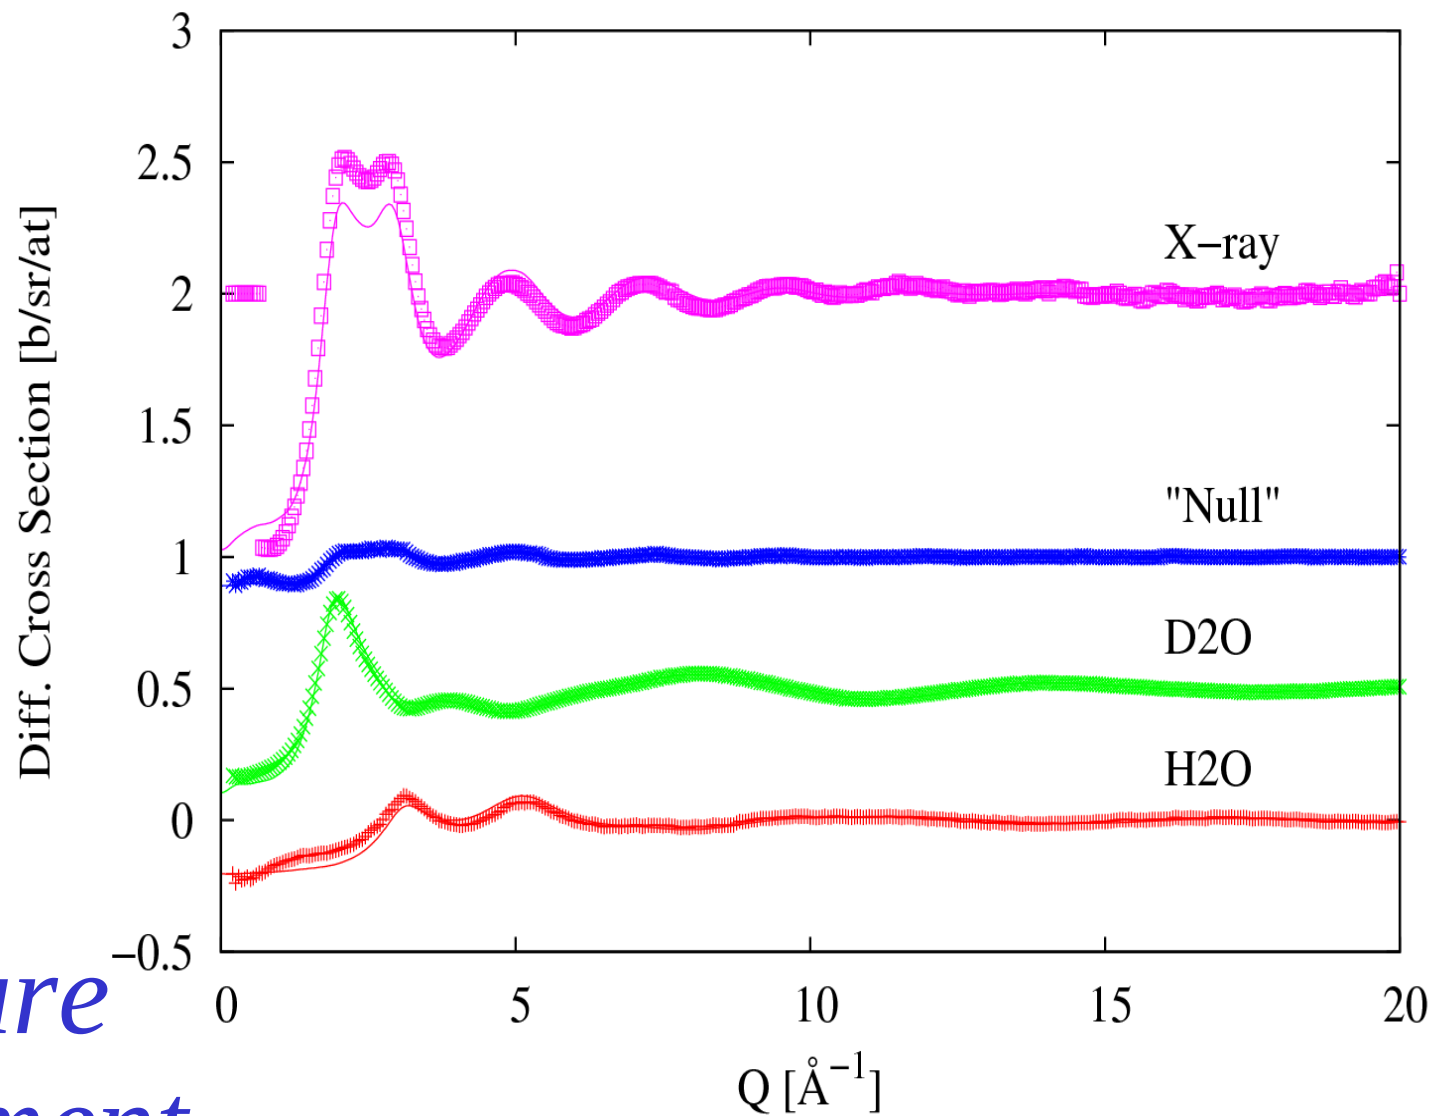

Water partial $g(r)$'s

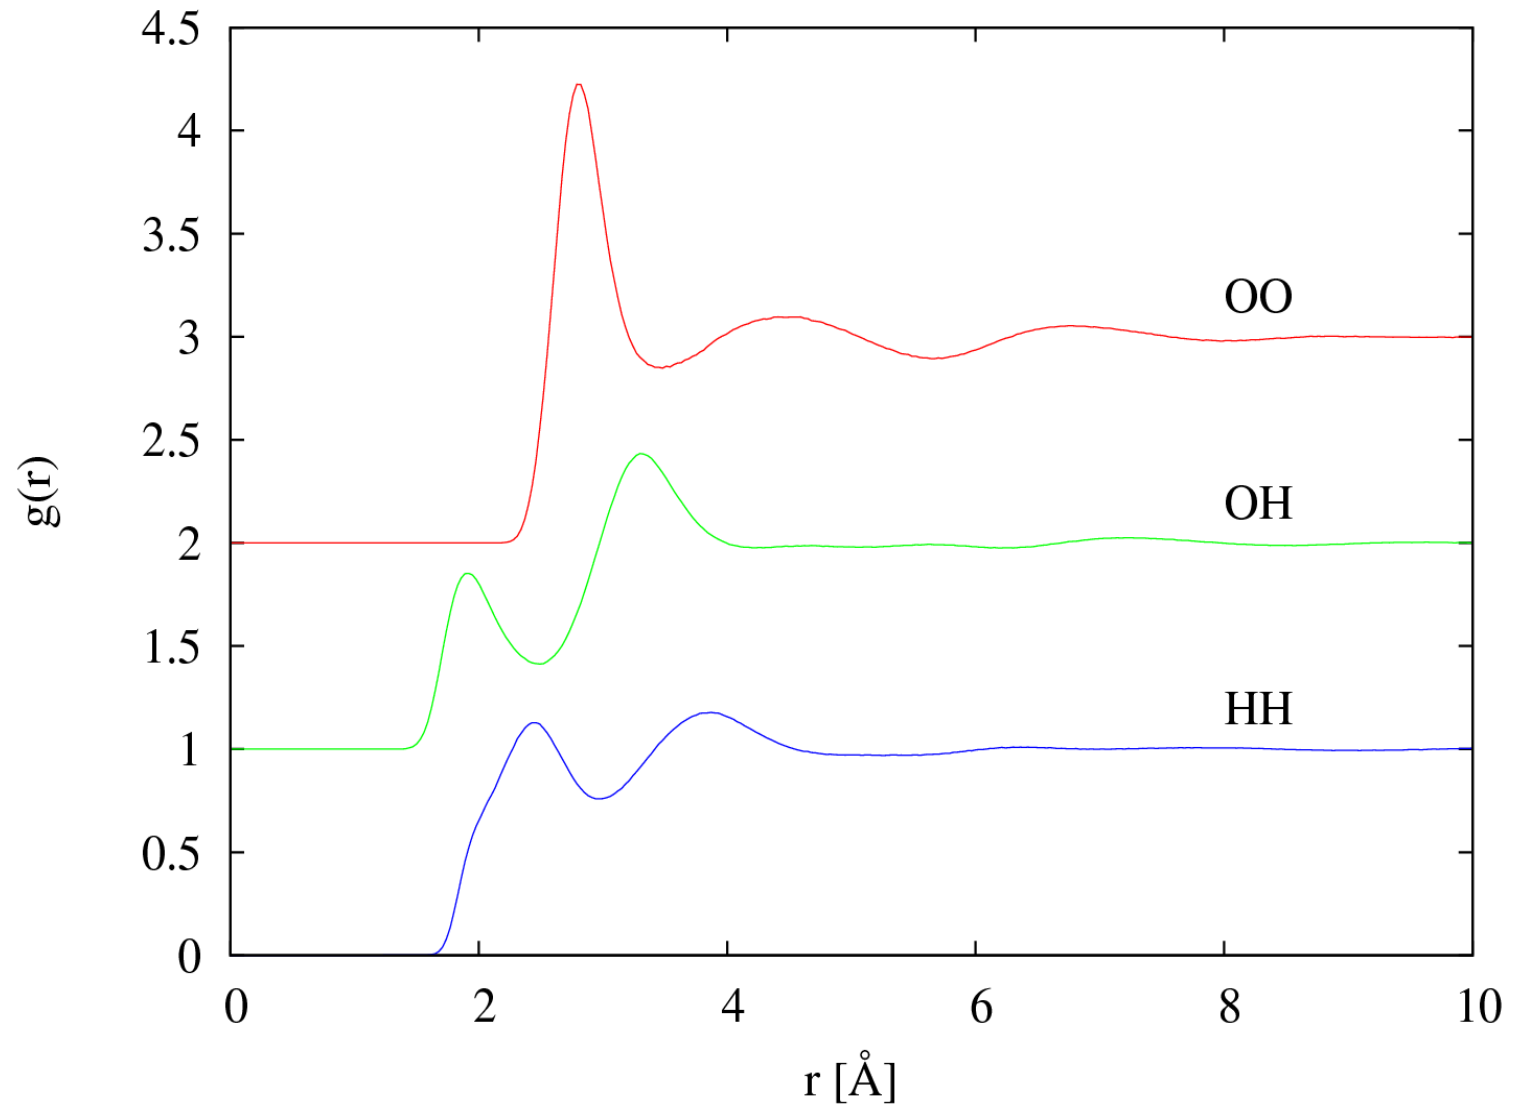


Water empirical potentials

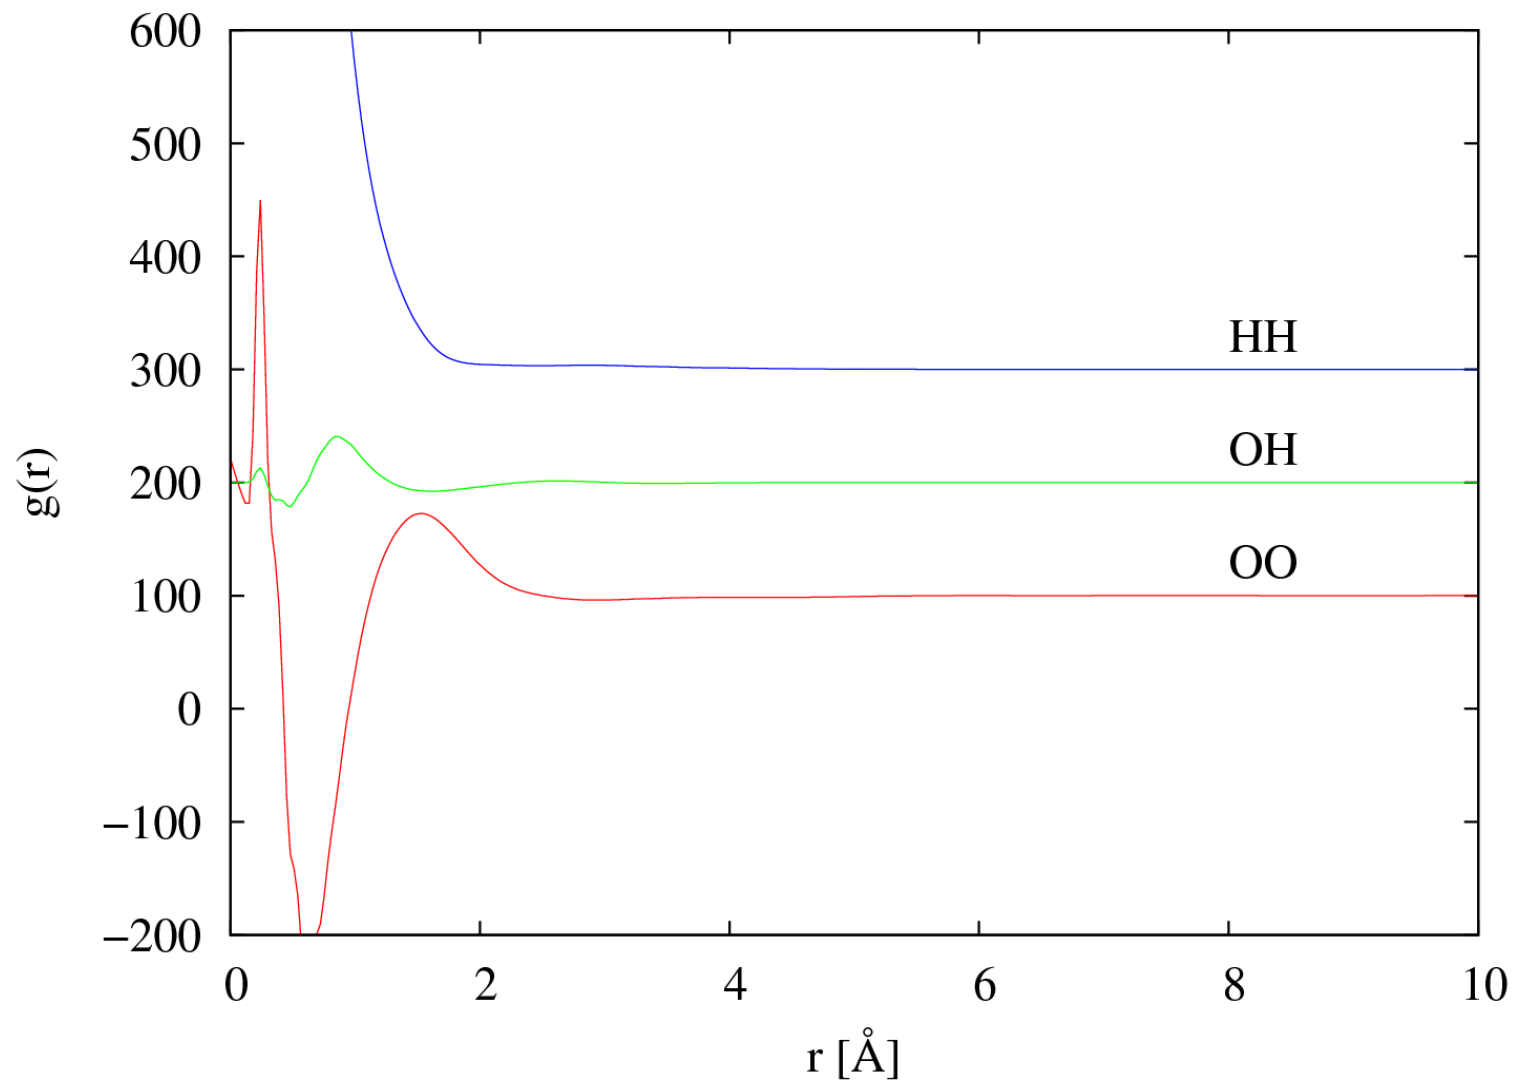


*The spatial density function of
water...*

Water structure

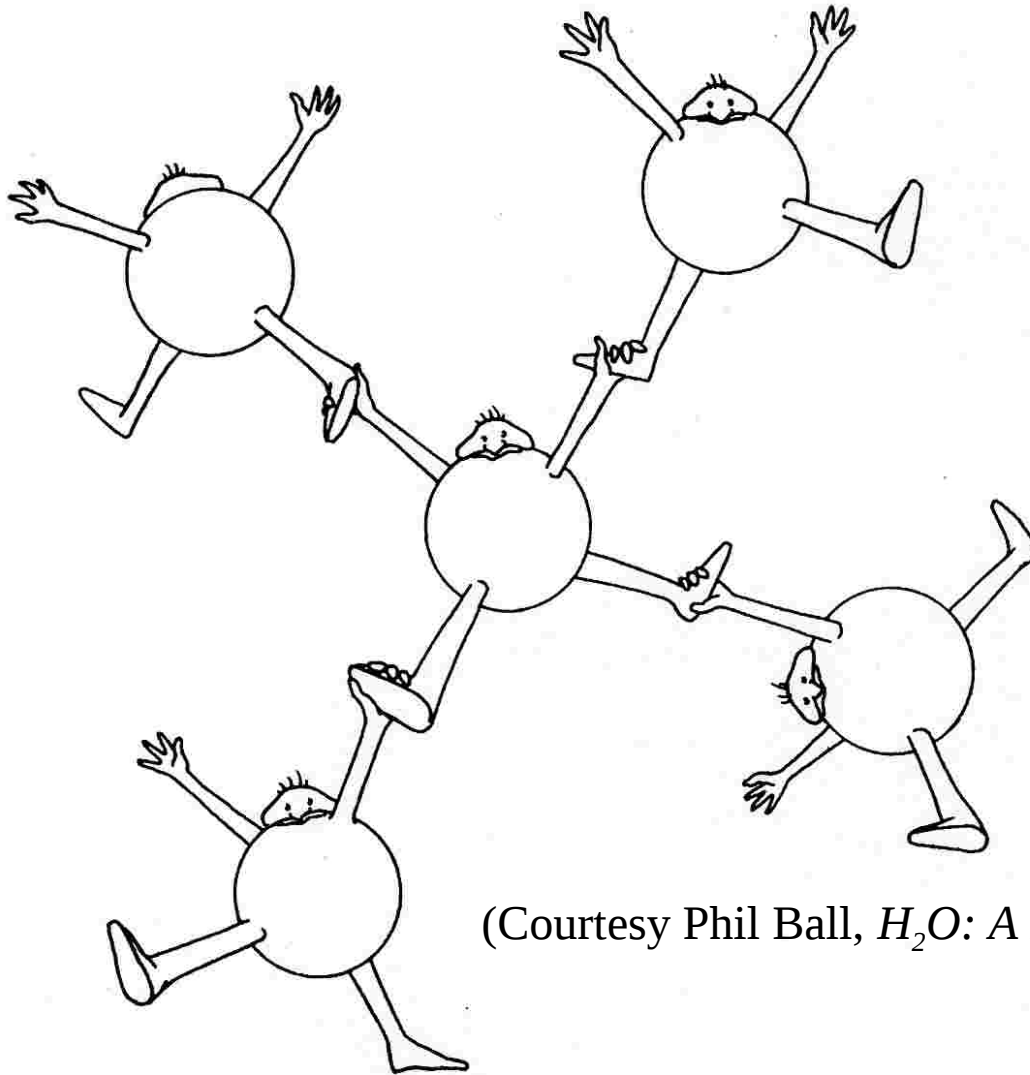

(Courtesy Phil Ball, *H₂O: A Biography of Water*)

Beyond $g(r)$: the spatial density function


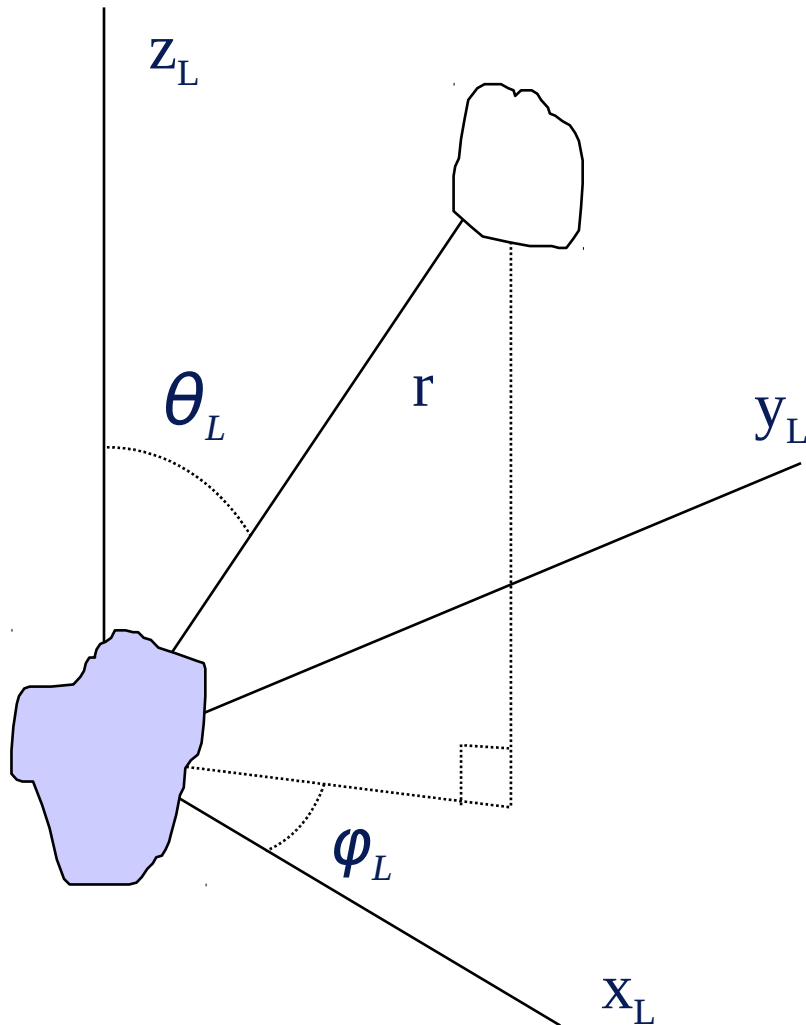


Choose distance range (0-5.7 Å)



and a contour level

(% of all molecules in distance range)



1%

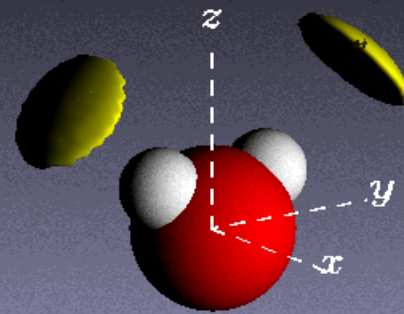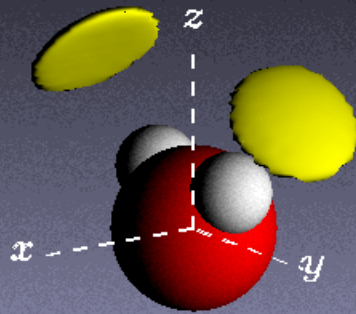



2%

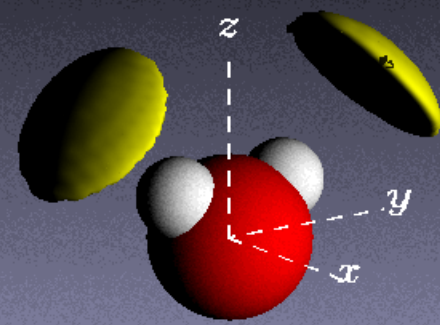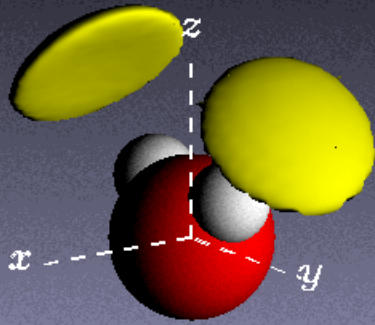



3%

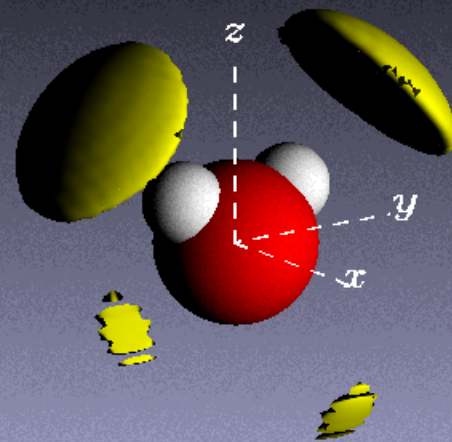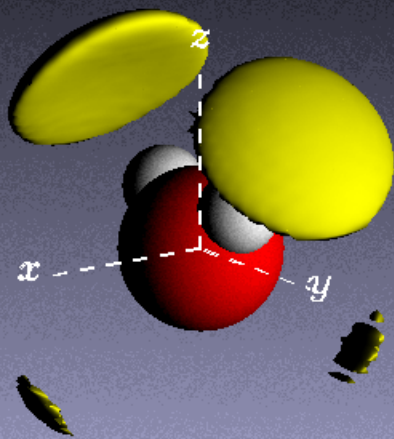



4%

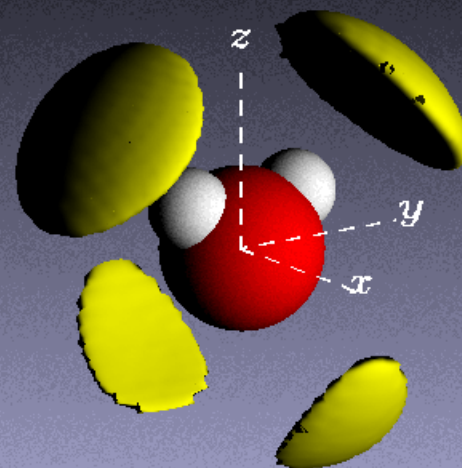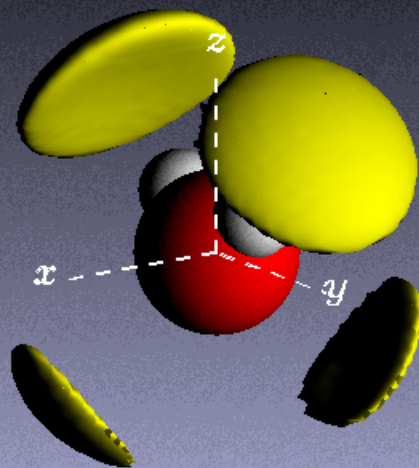



5%

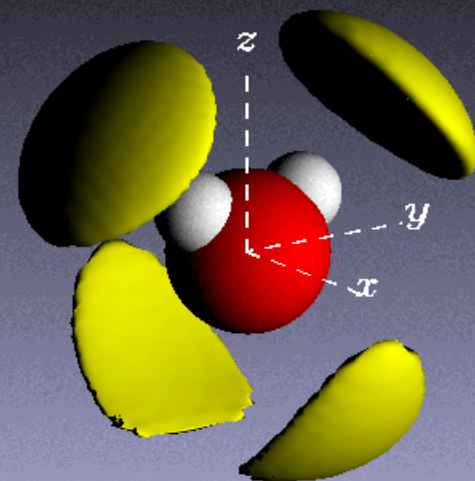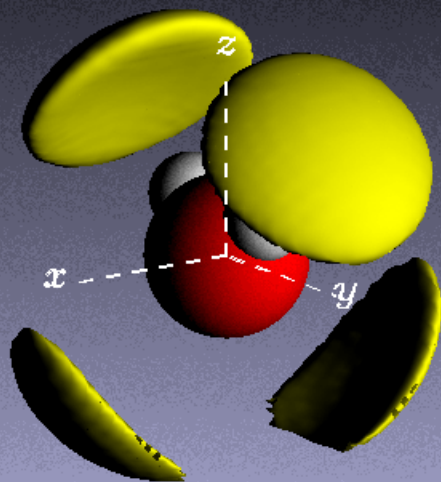



7%

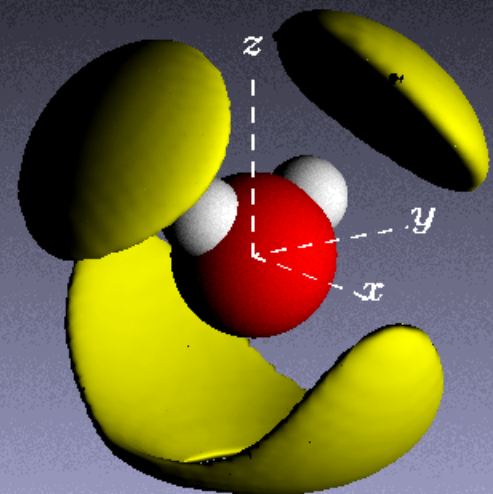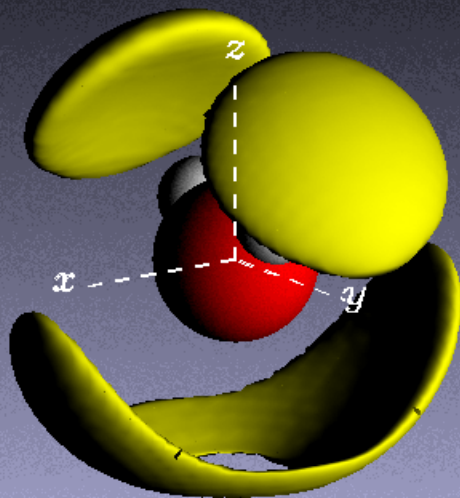



9%

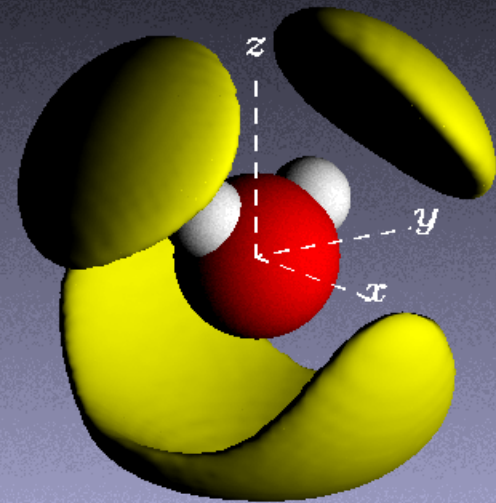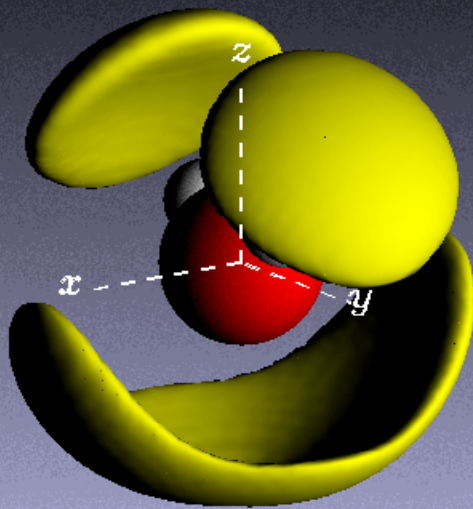



12%

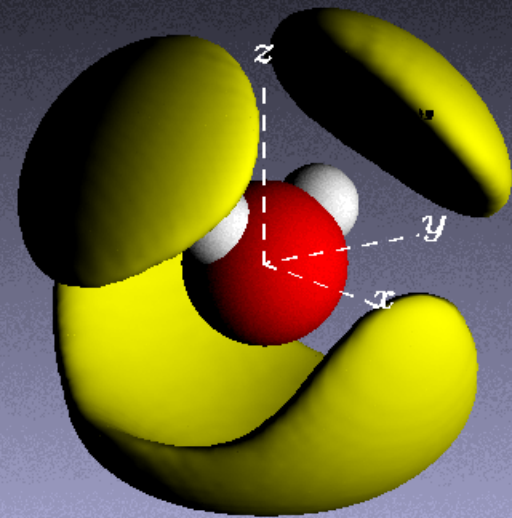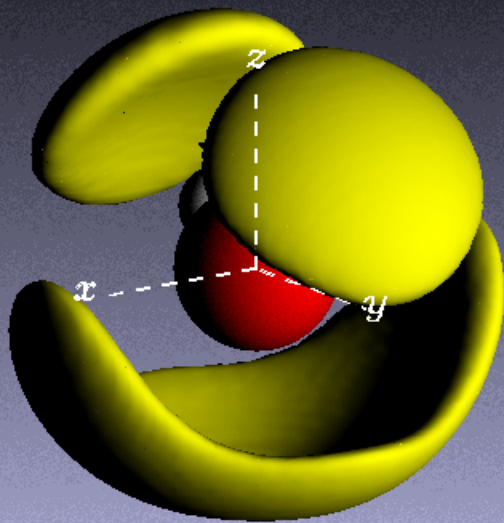



15%

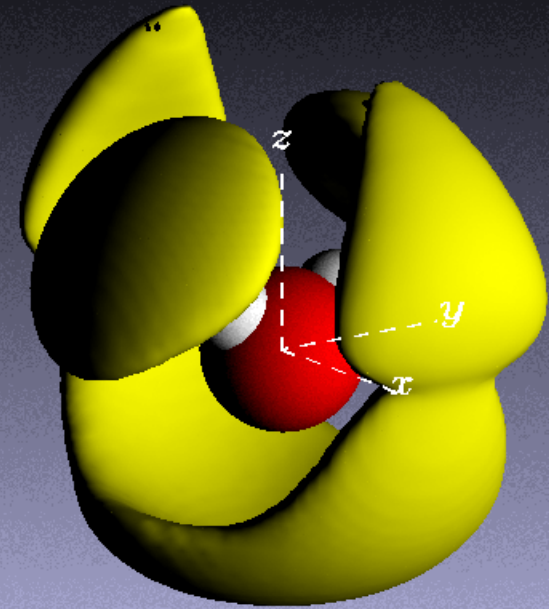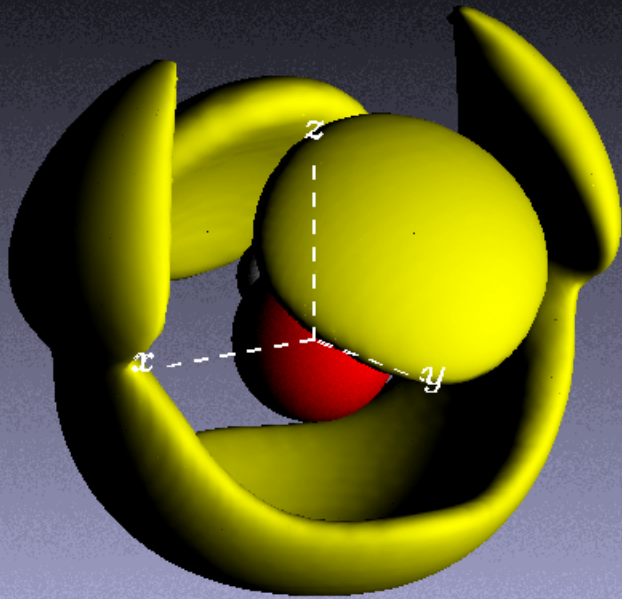



18%

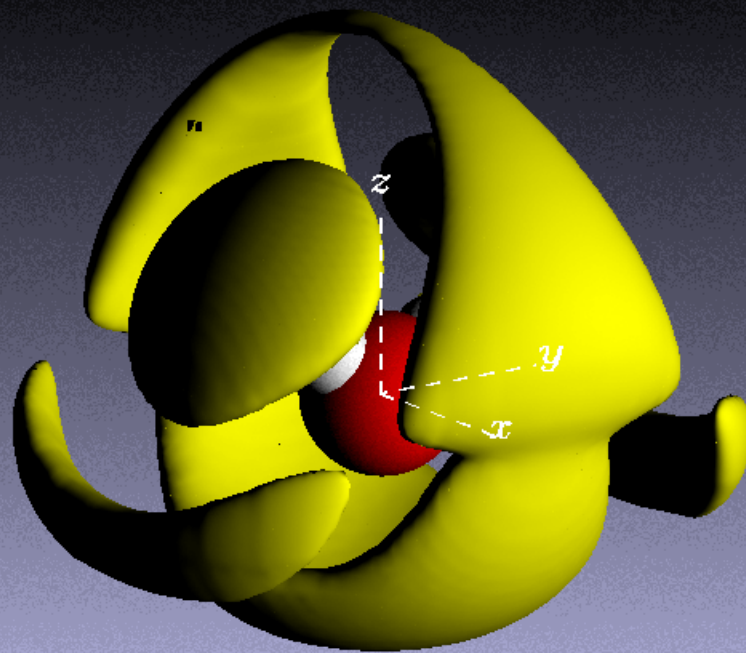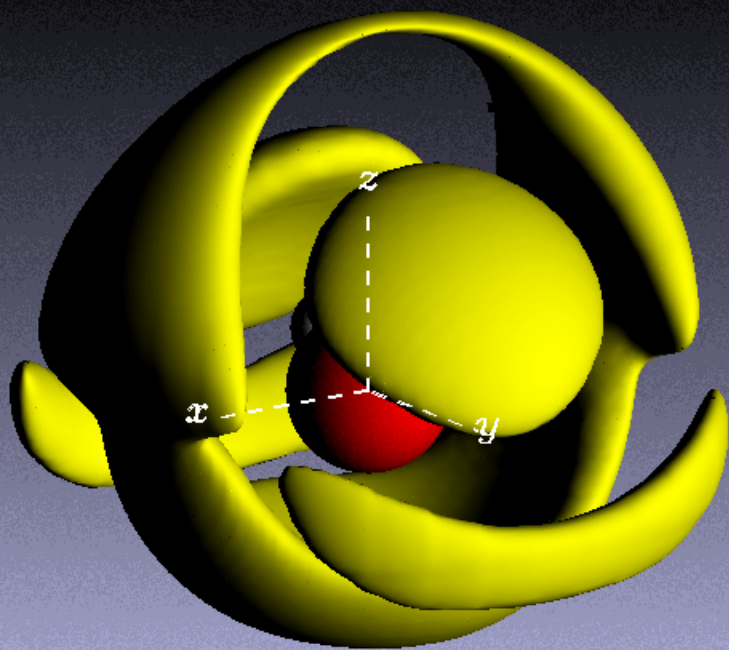



21%

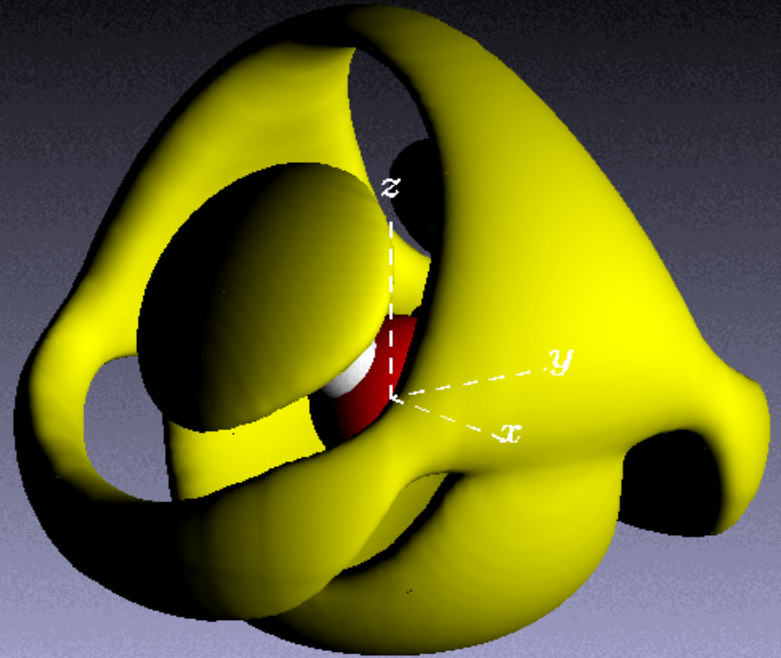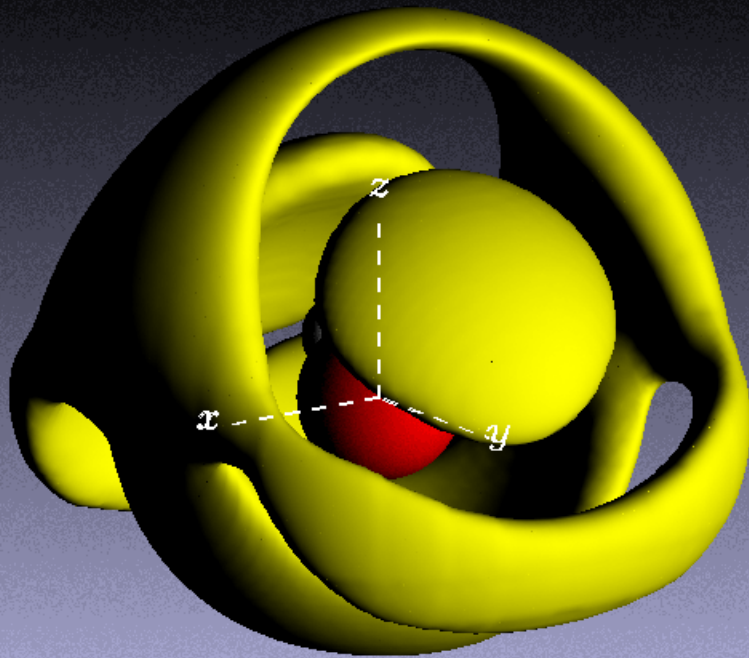

25%

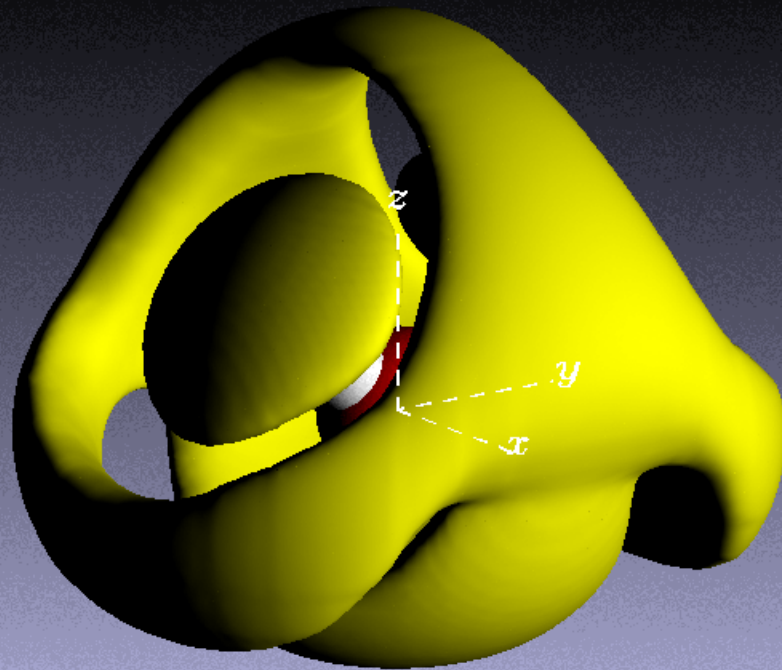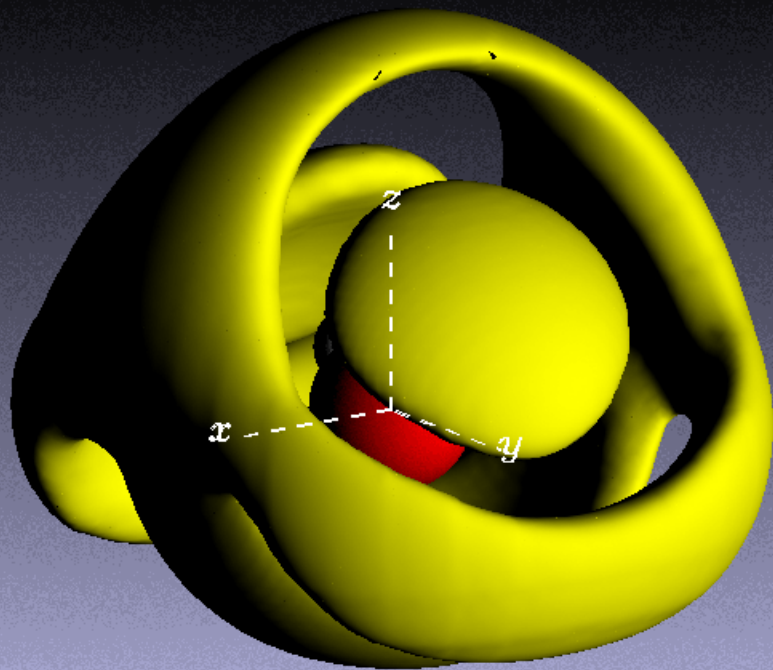


30%

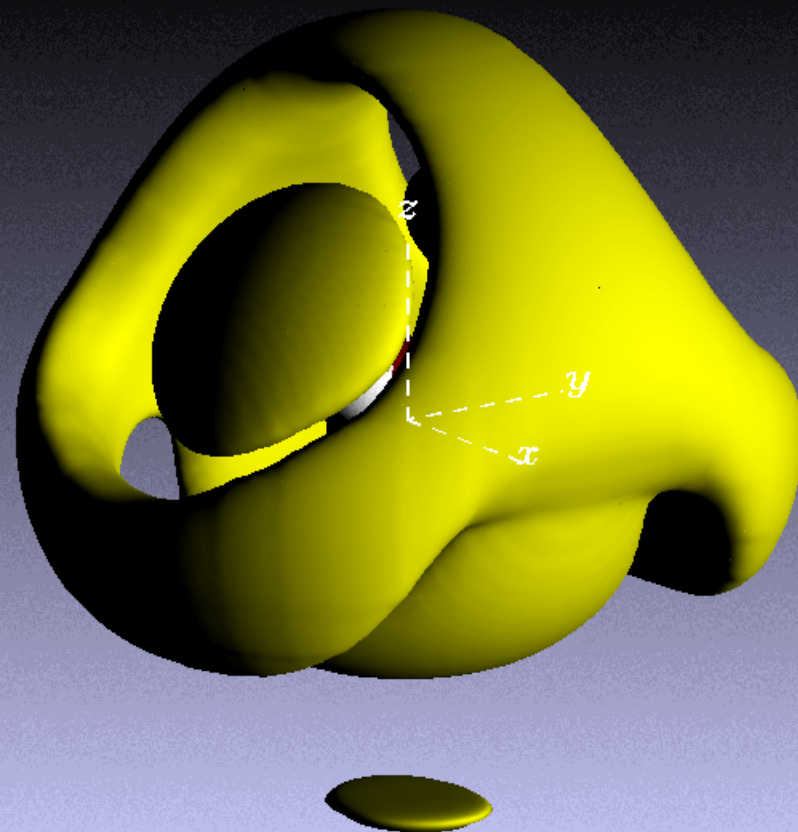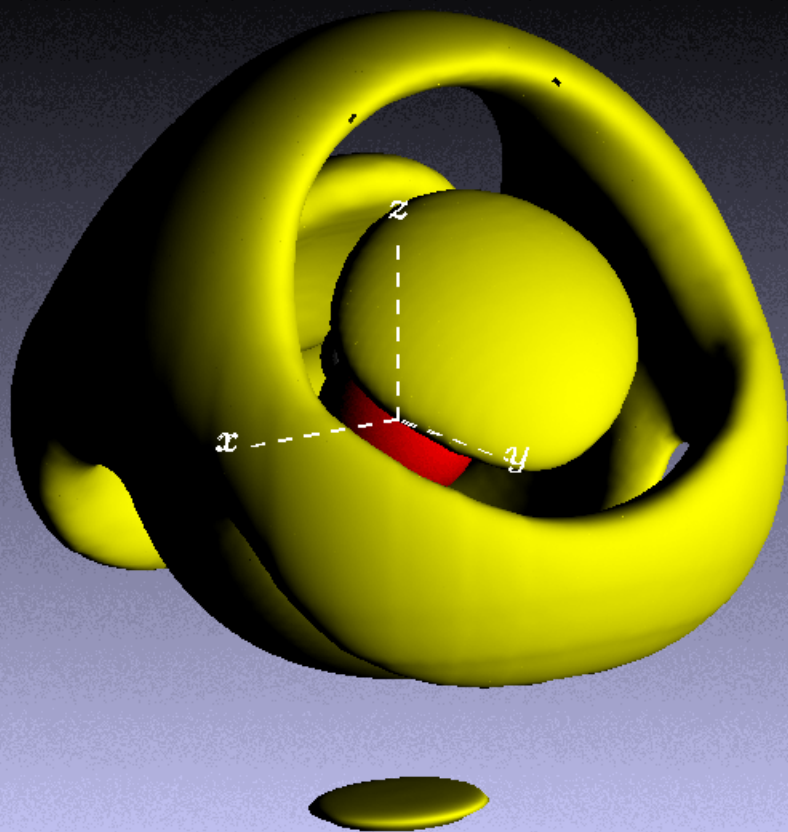


Water under pressure


$g_{OO}(r)$'s for water at 268K

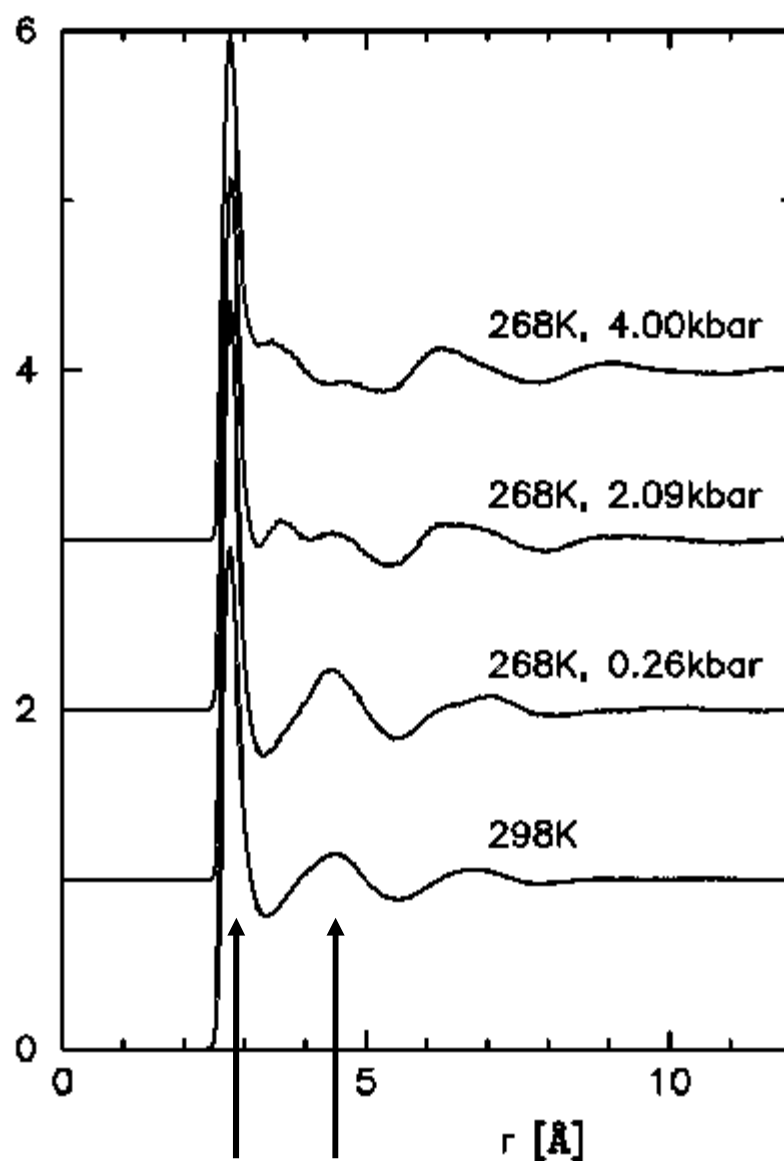


Water at 298K, 0kbar

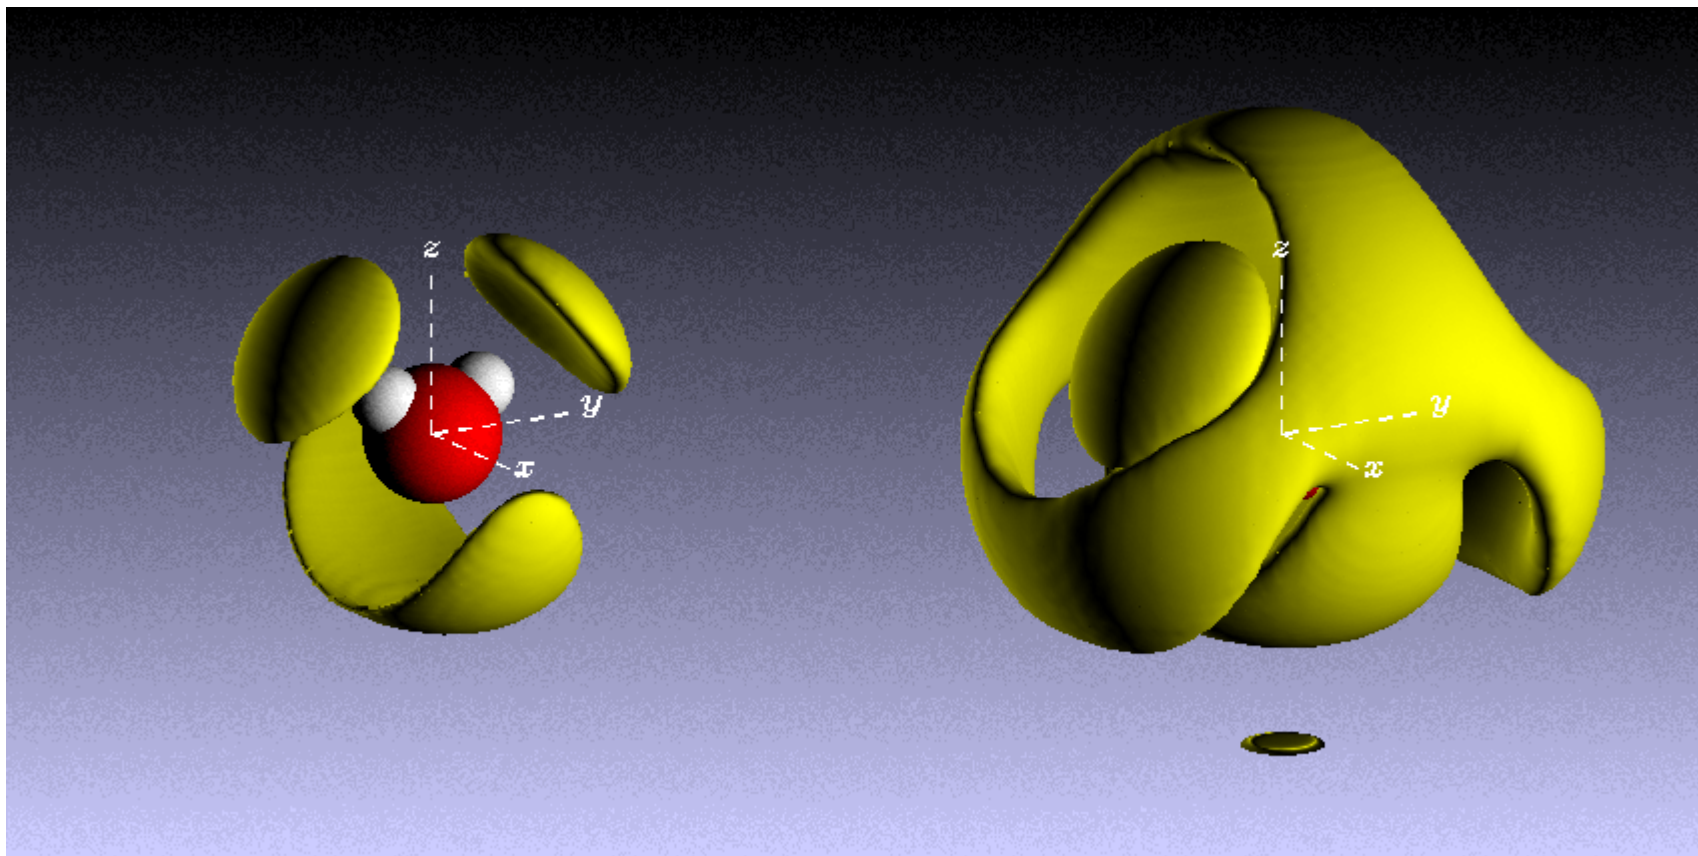


Water at 268K, 0.26kbar

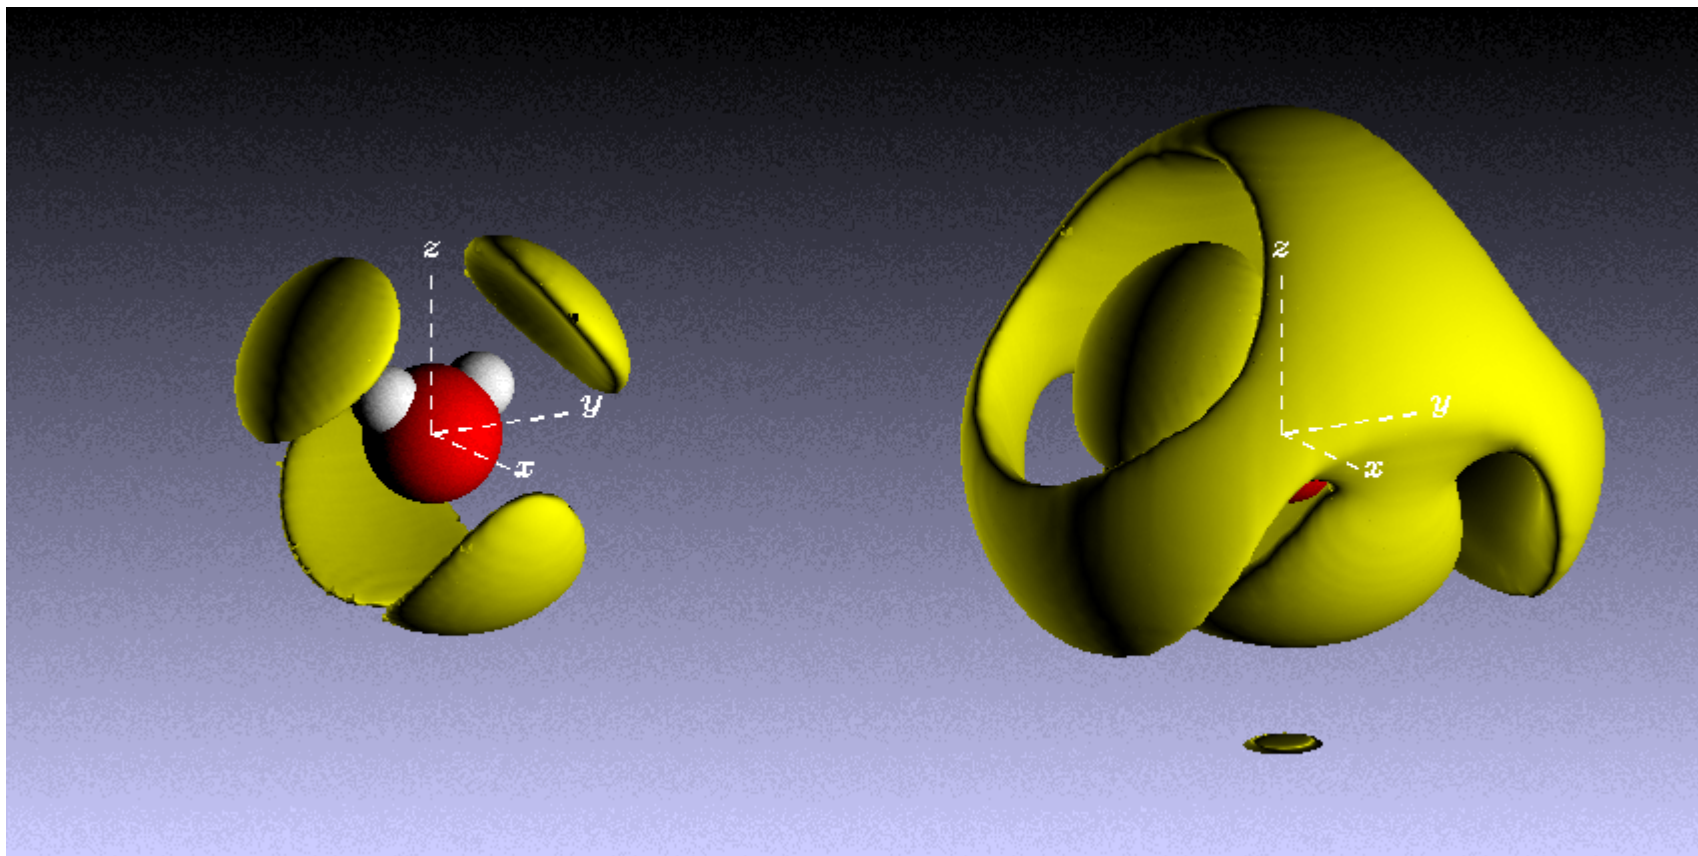


Water at 268K, 2.09kbar

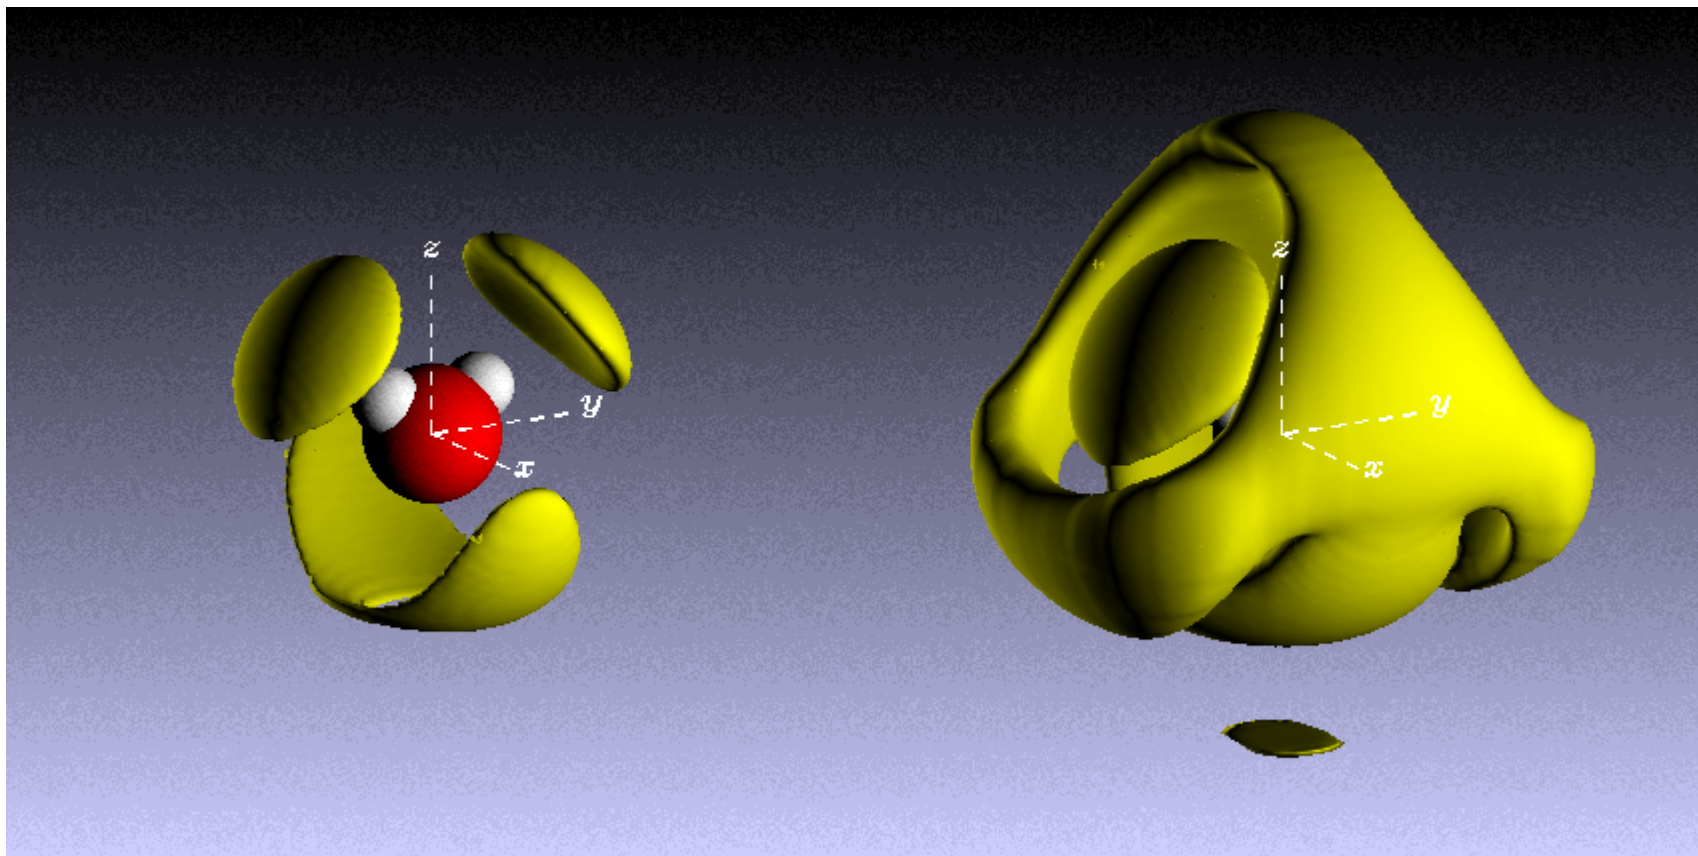


Water at 268K, 4.00kbar

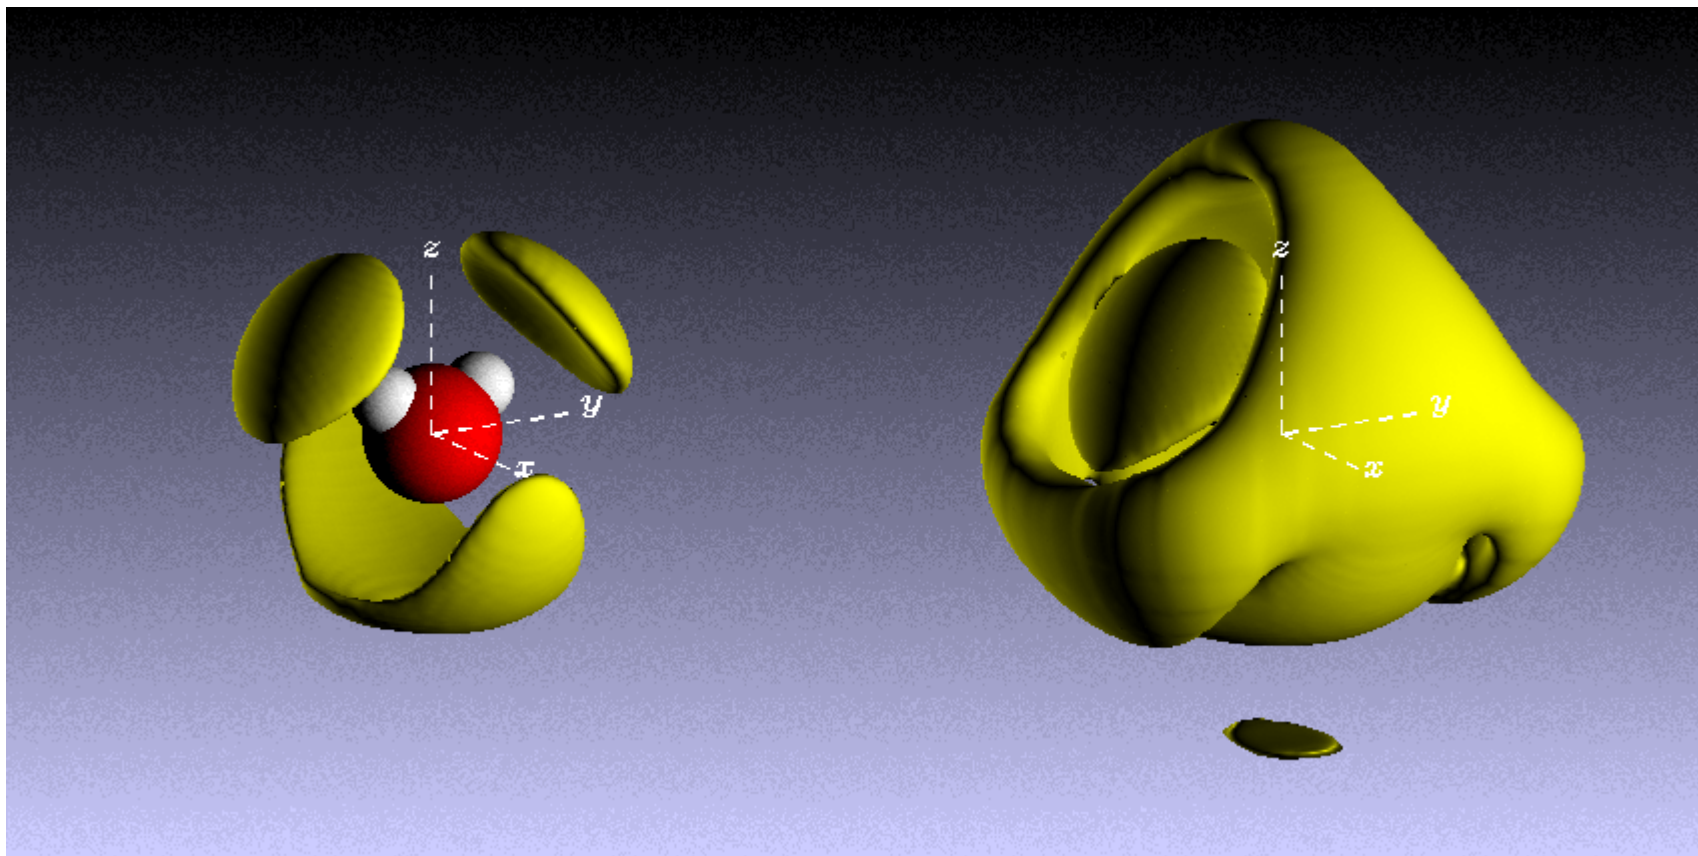


Bond angle distributions

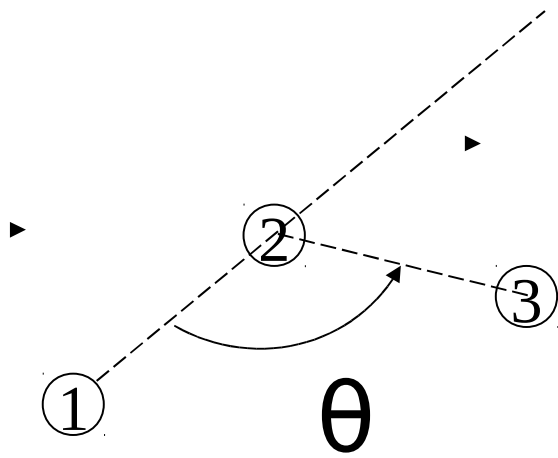


Or:-

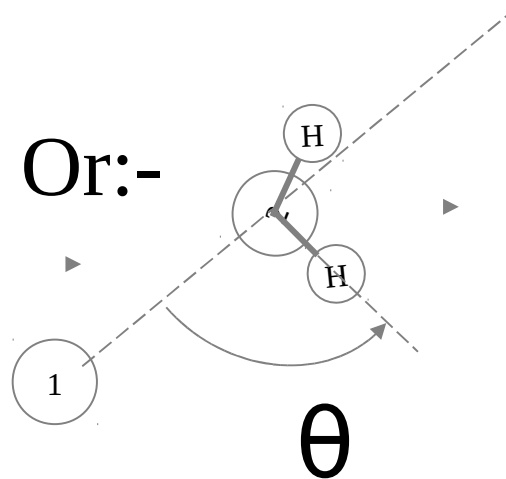


Or:-

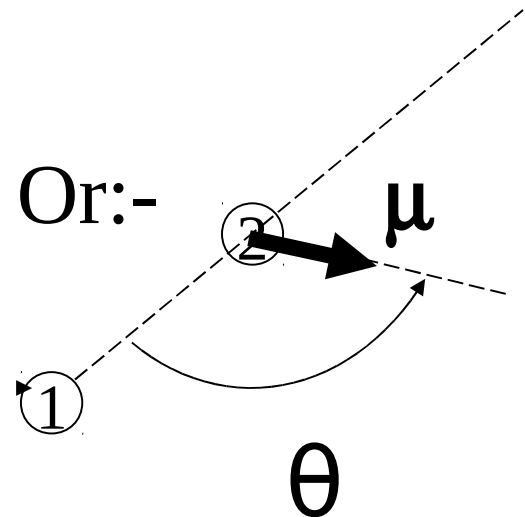


O-O-O angle distribution

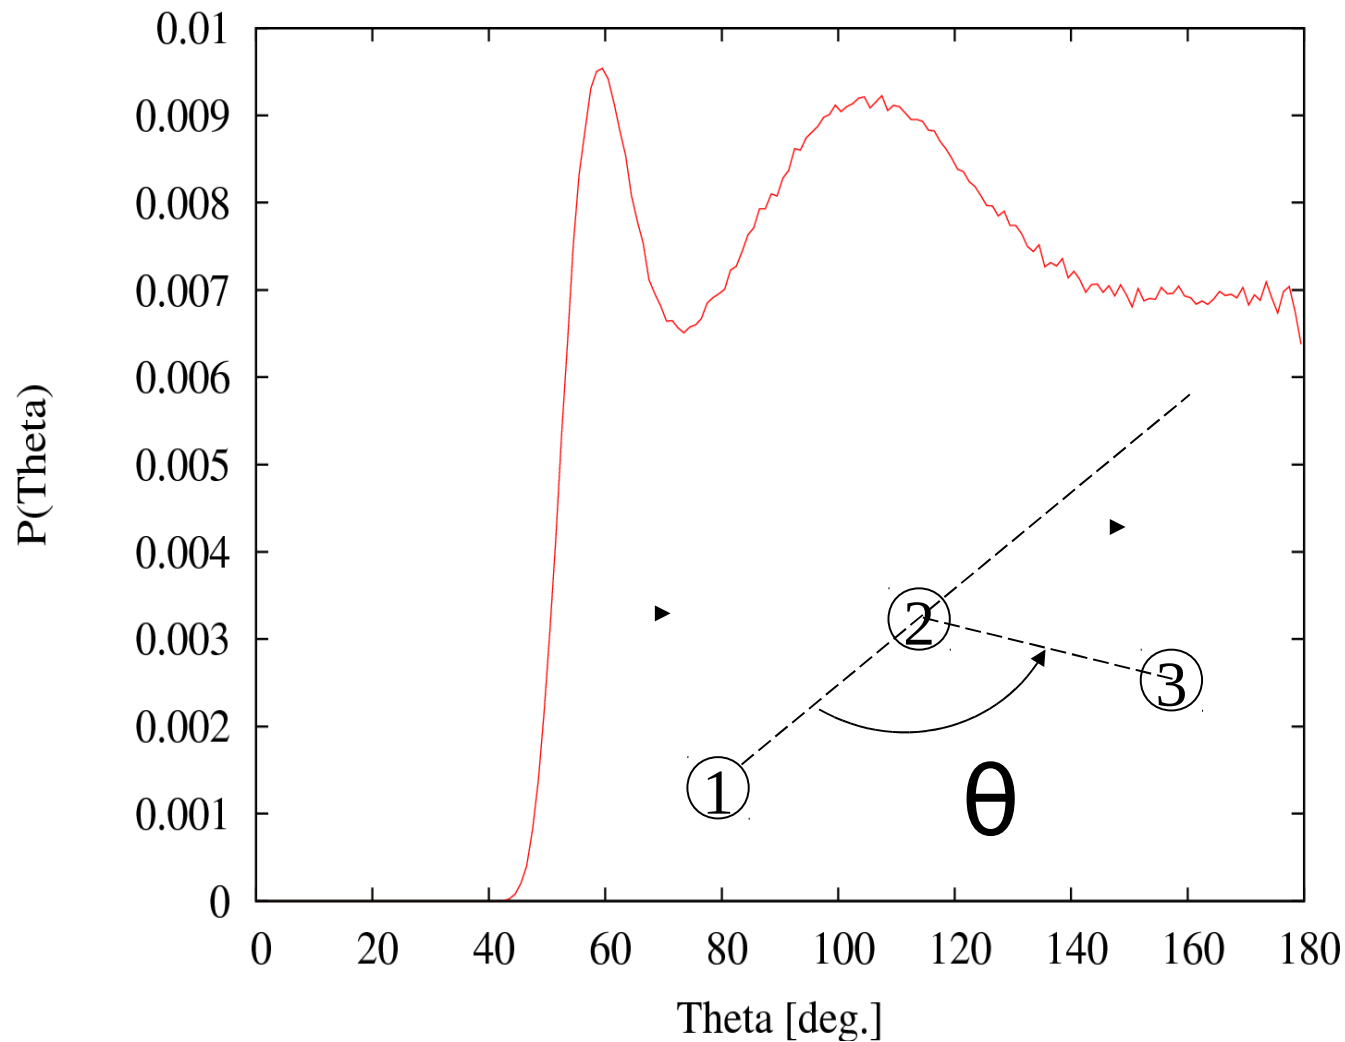


O-O-H angle distribution

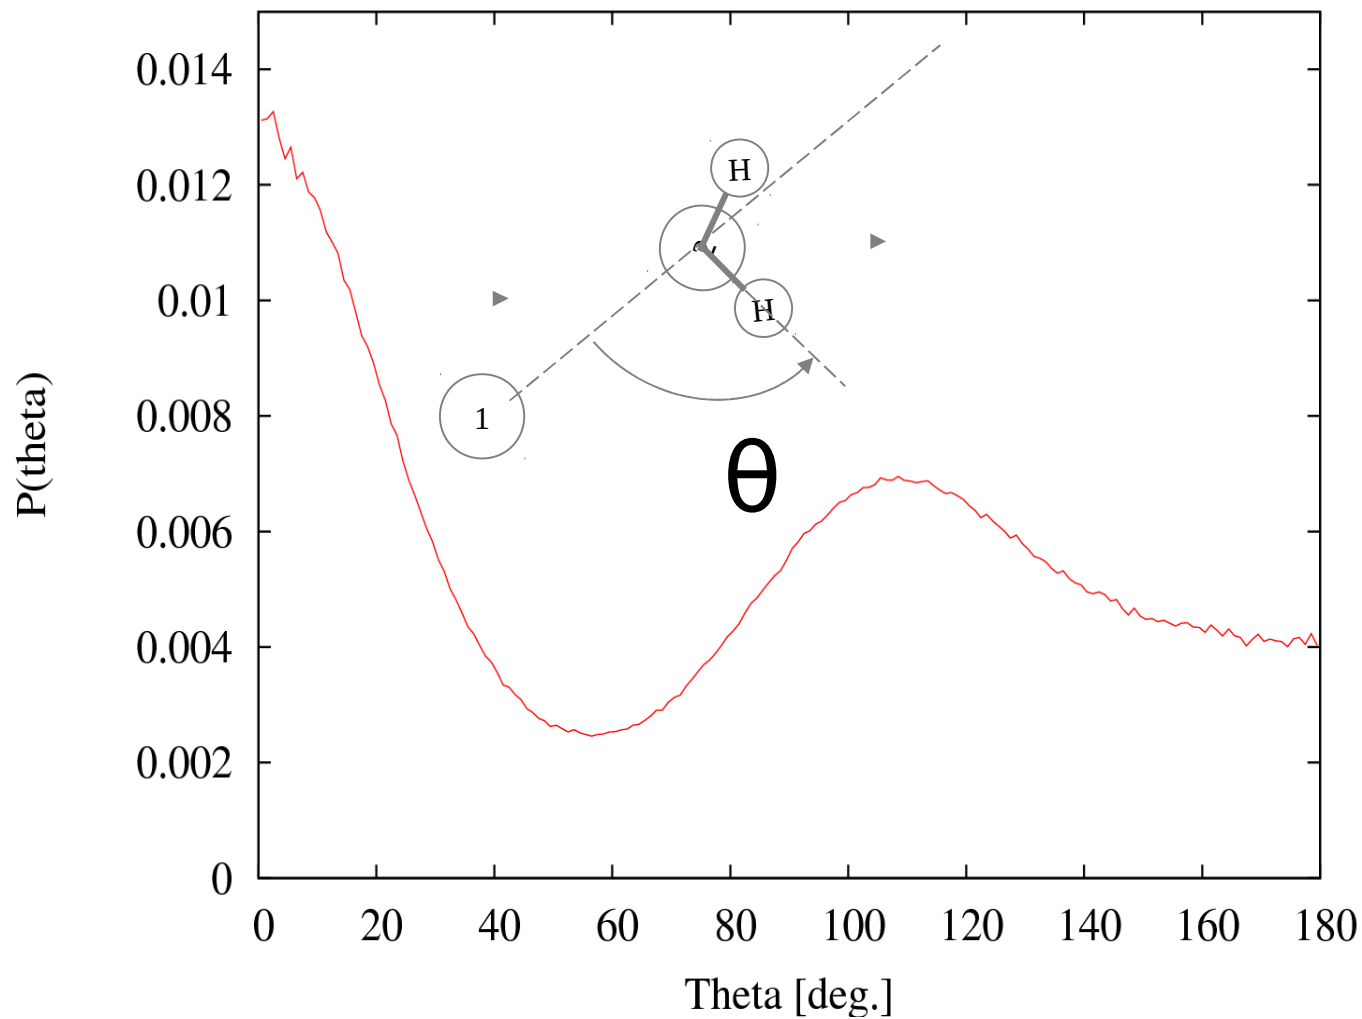


$O\text{-}\mu$ angle distribution

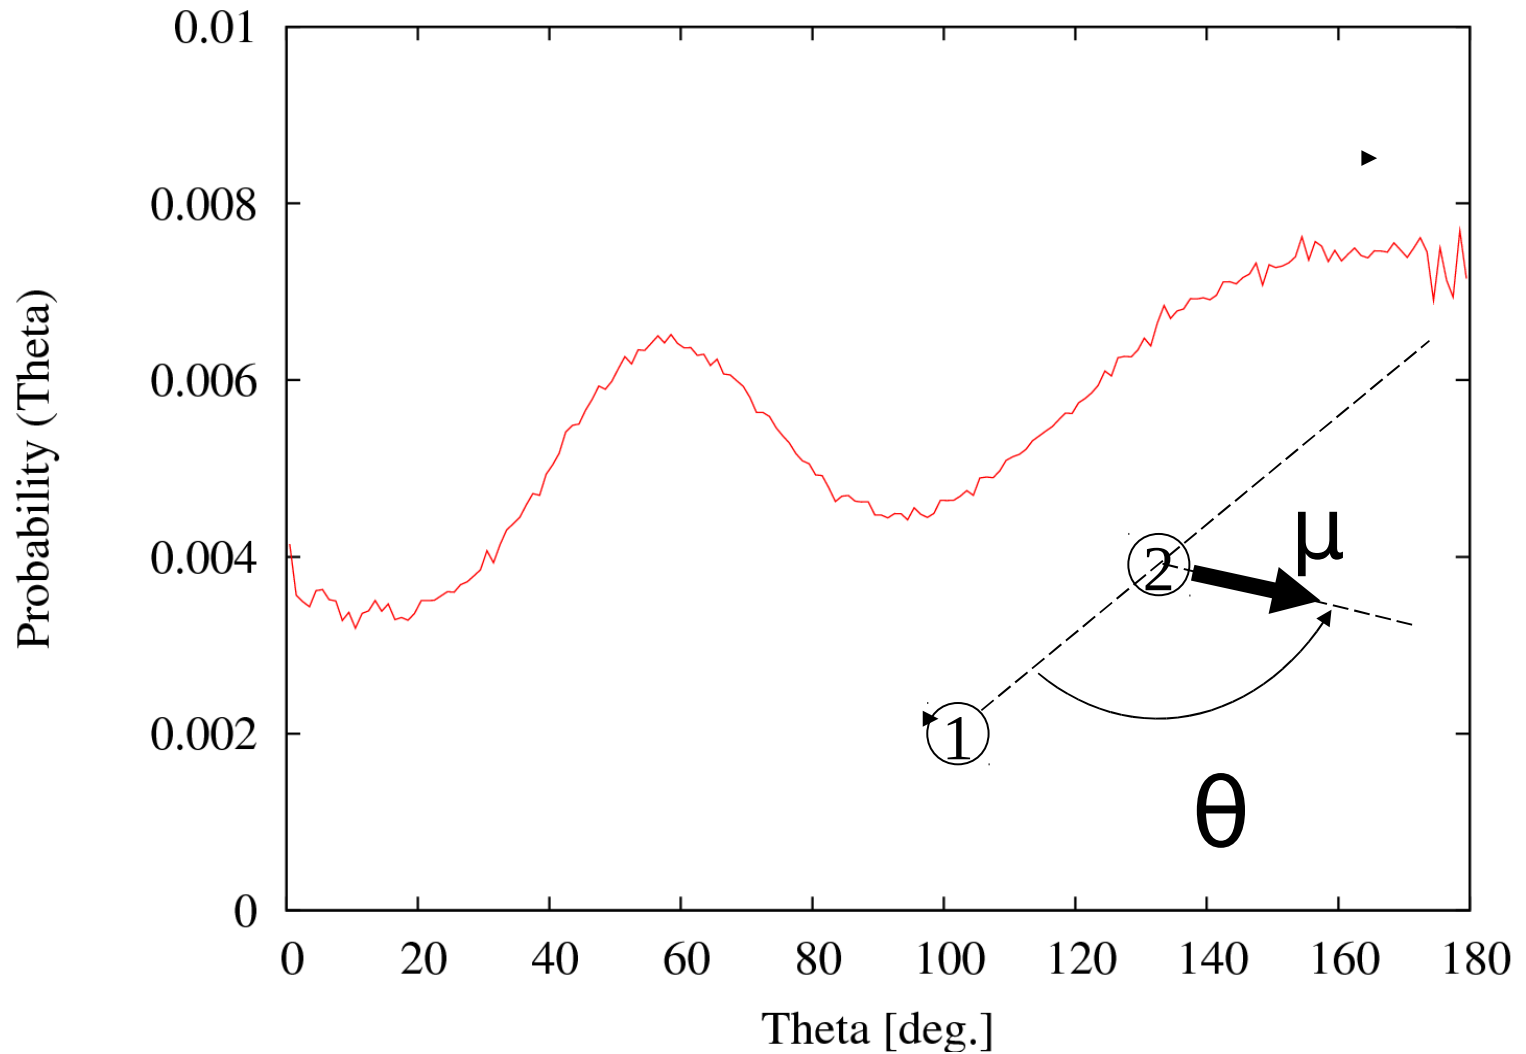

A step further: the orientational pair correlation function

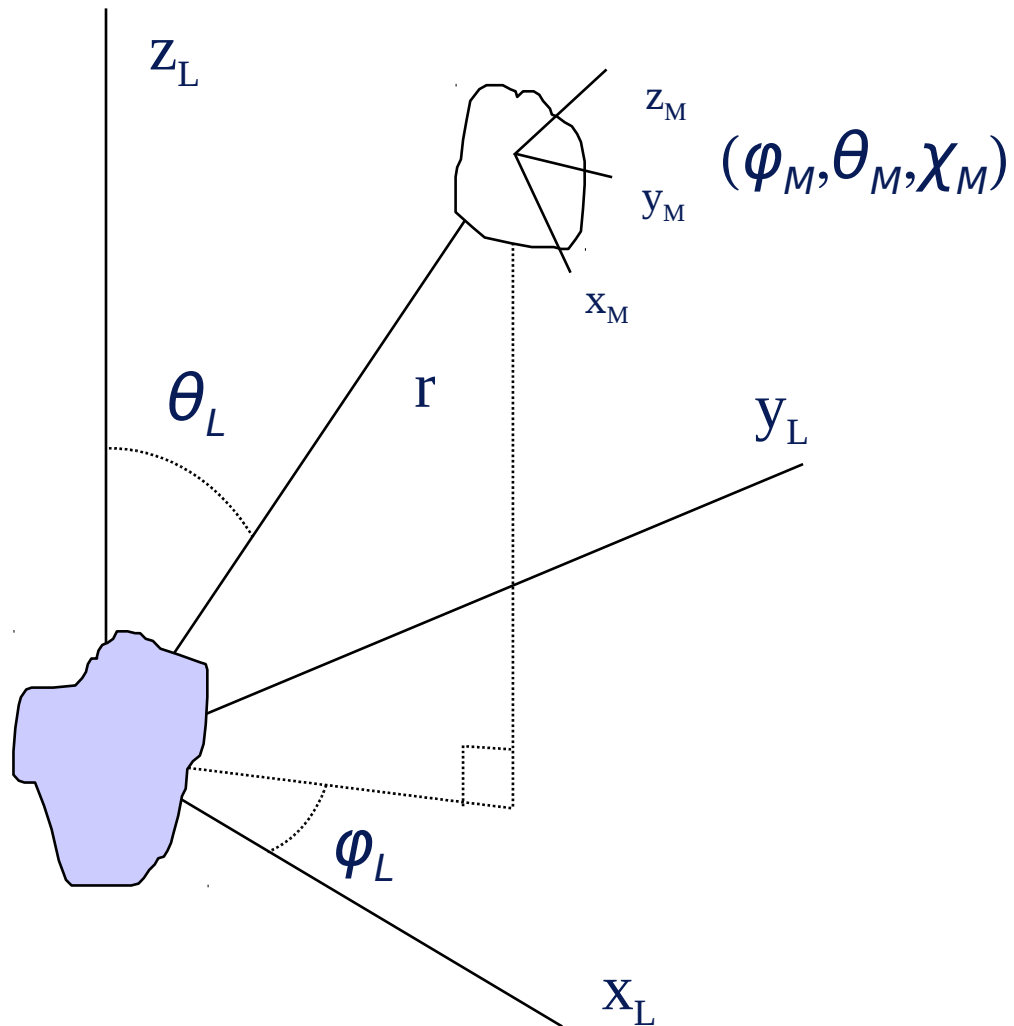


Dipole orientations in water

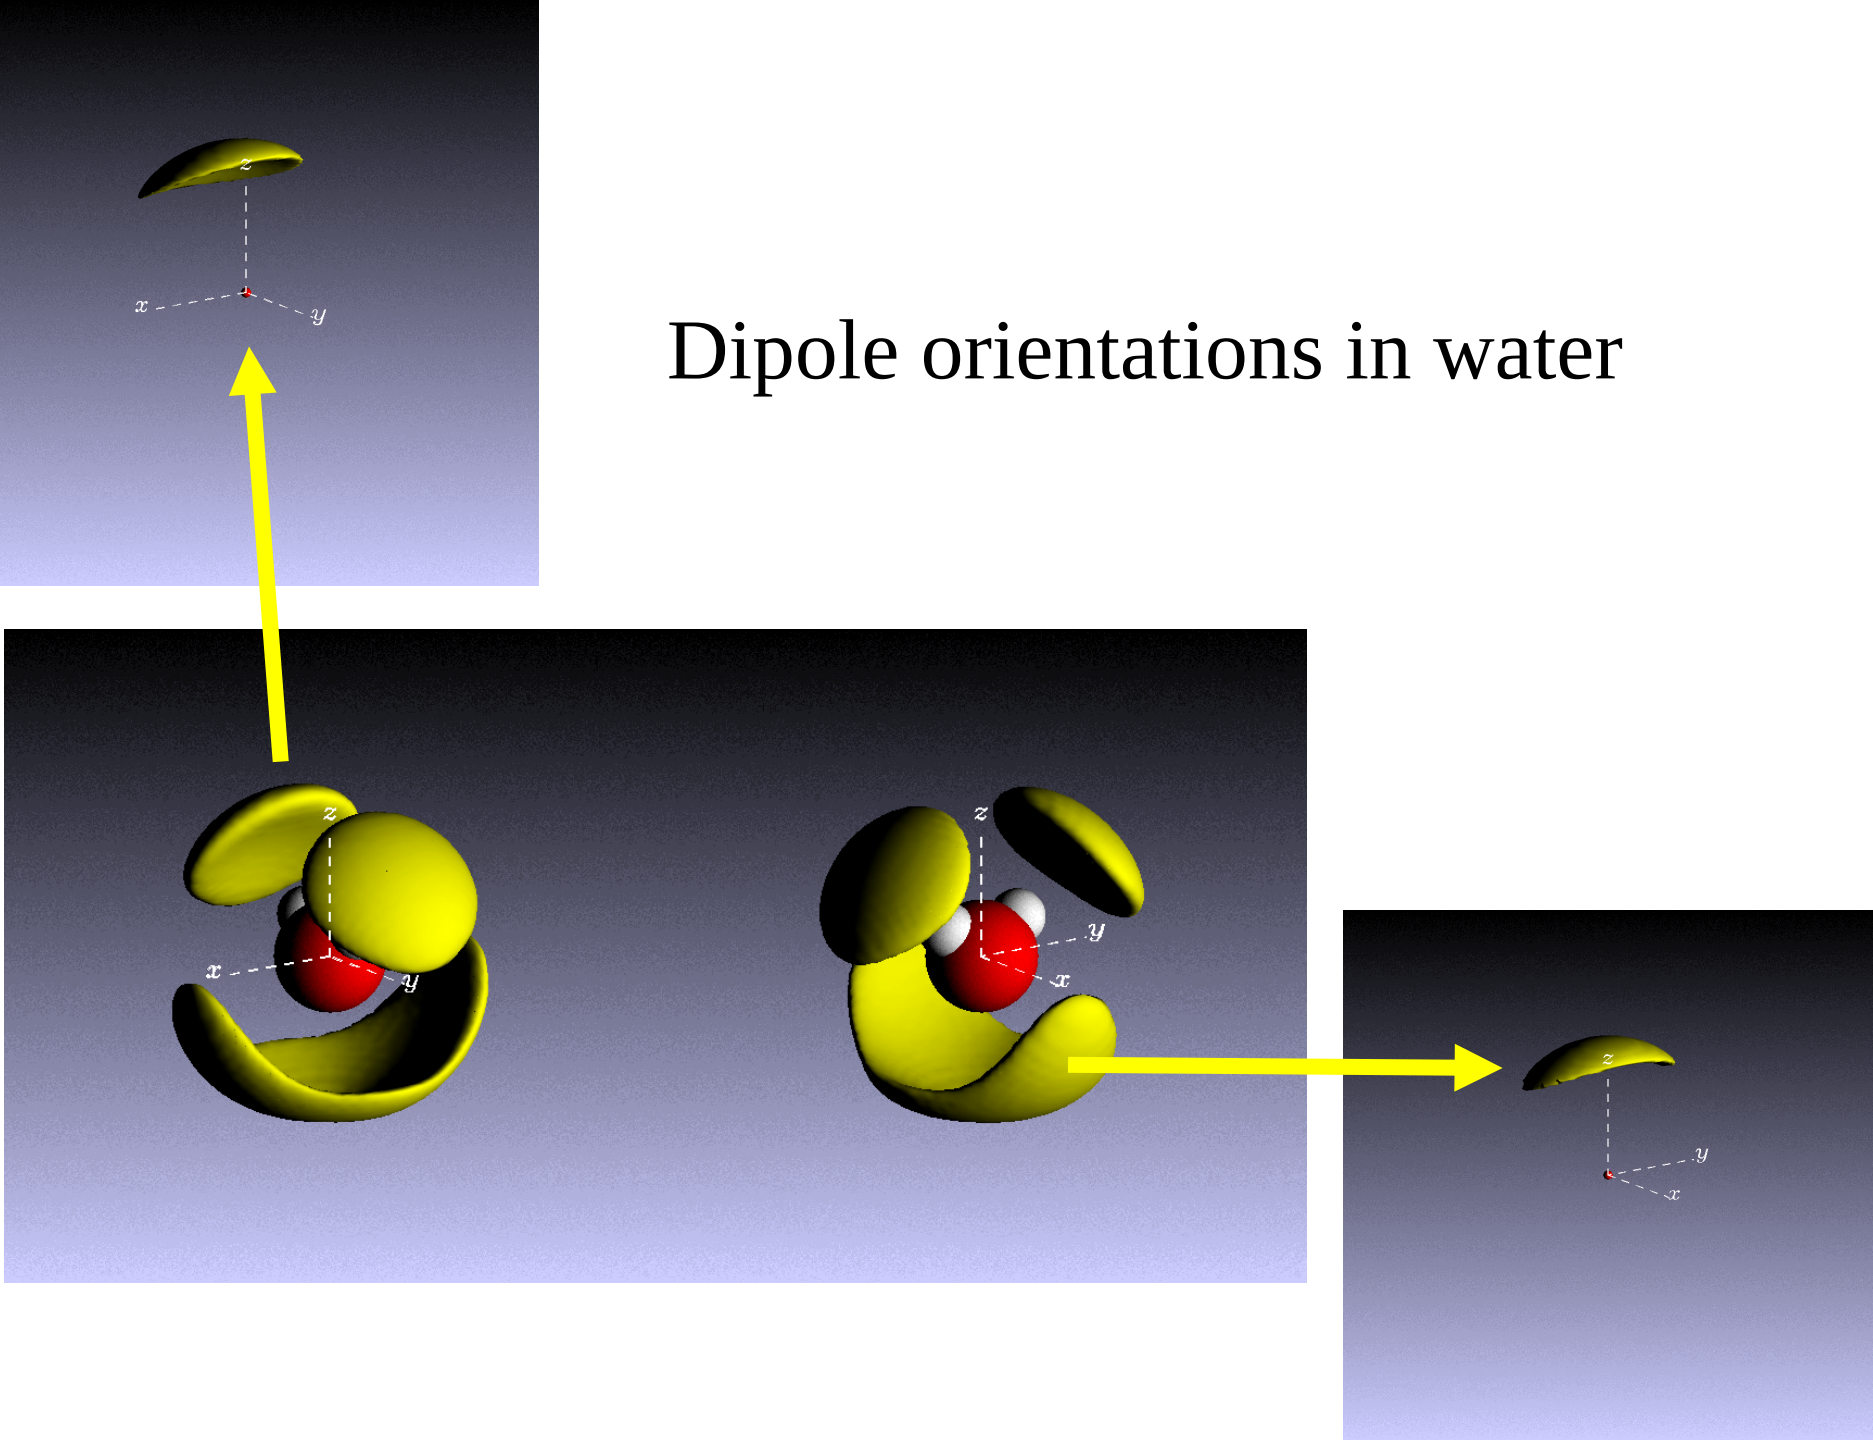

*Another
example:*


*Molten
 Al_2O_3*

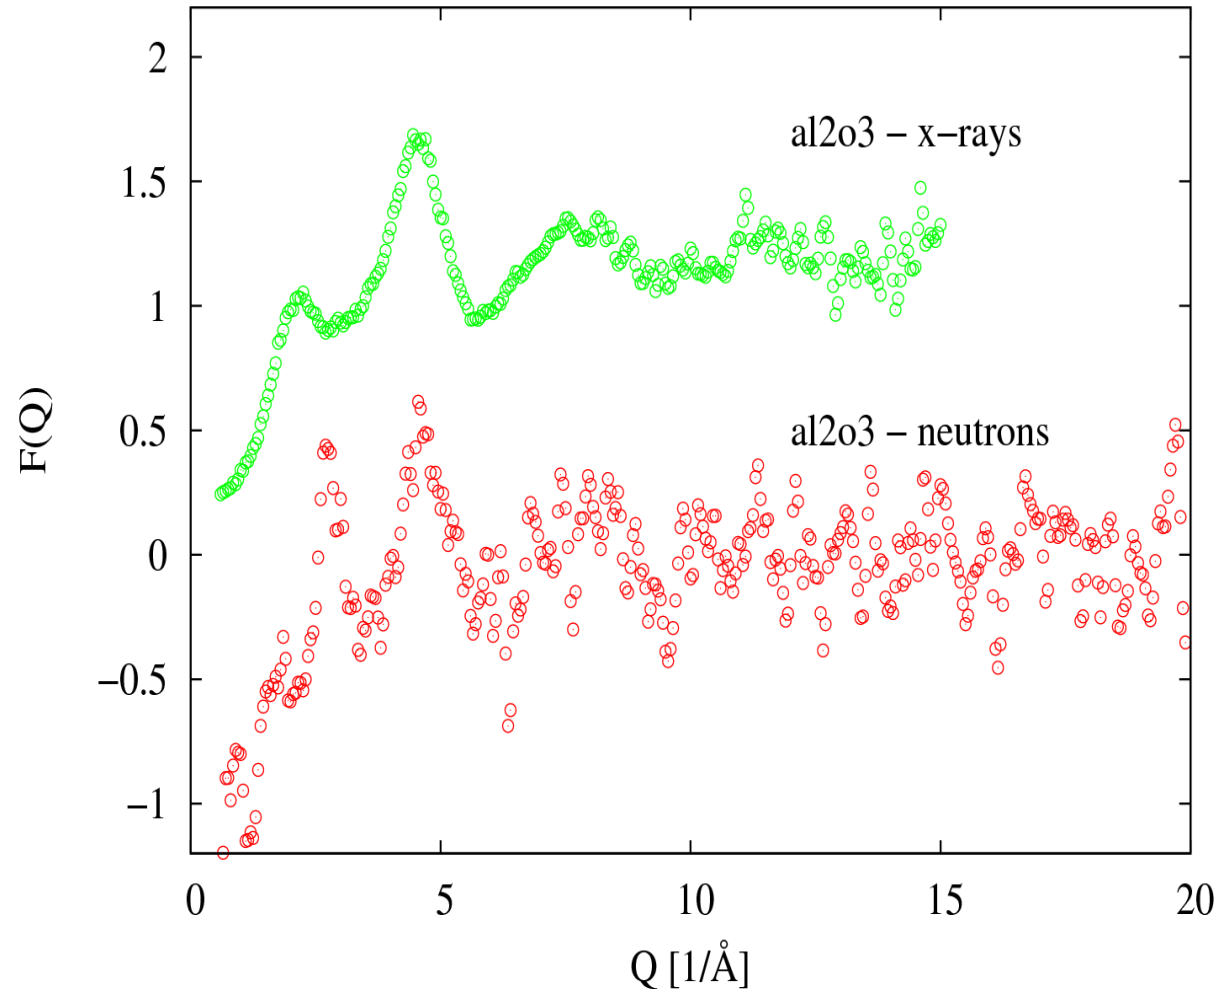


[Courtesy of
Neville Greaves
(Aberystwth)
and
Claude Landron
(Orleans)]

Molten Al_2O_3

*Final
fit
after
Empirical
Potential
Structure
Refinement*

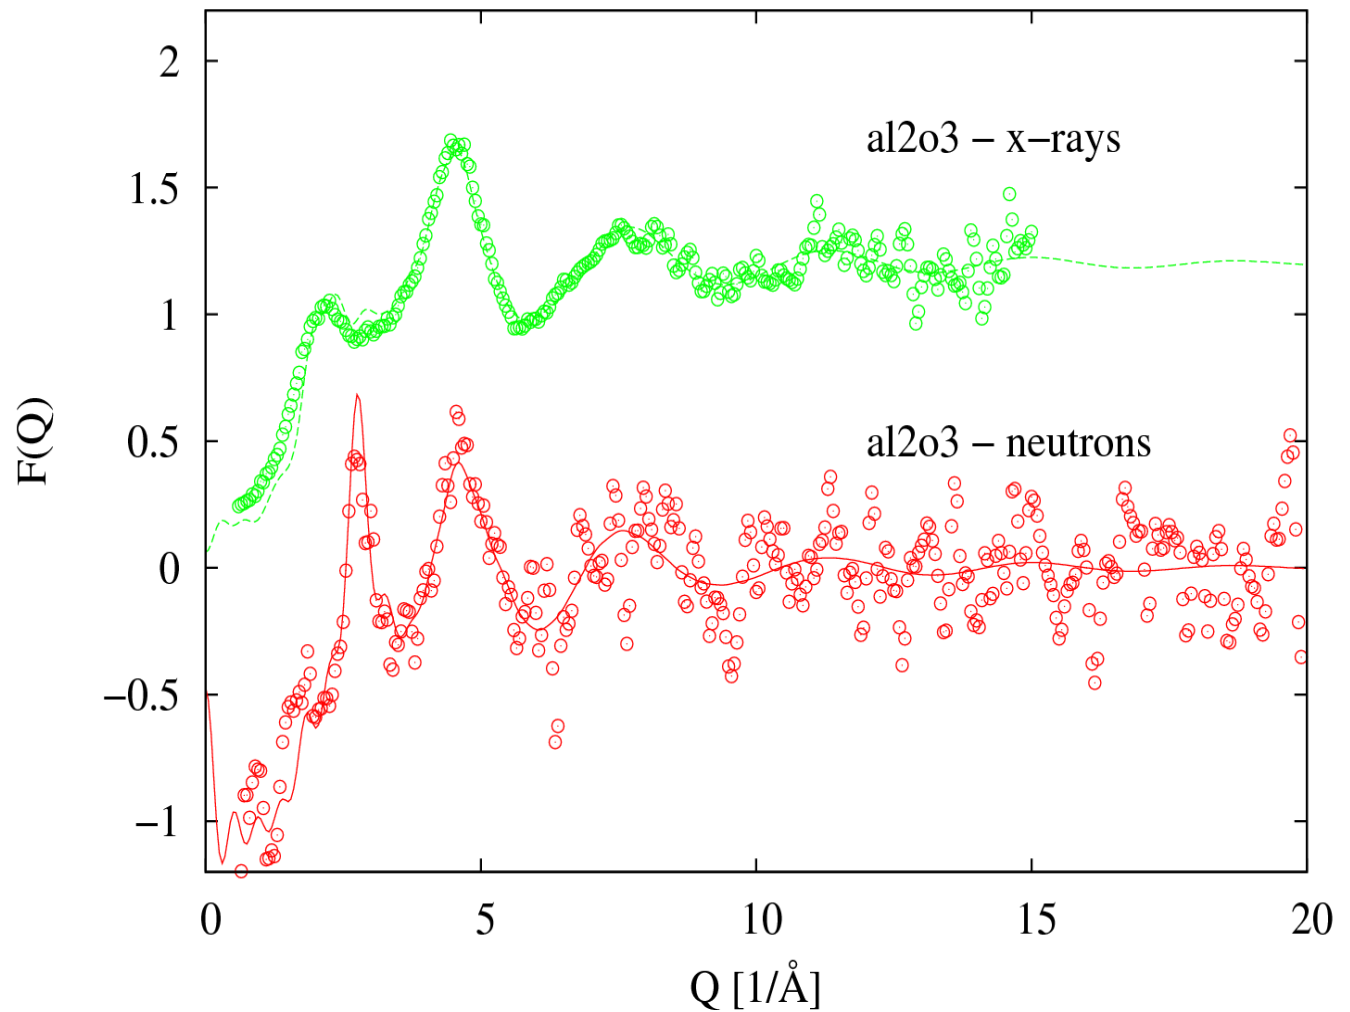


Partial $g(r)$'s for Al_2O_3

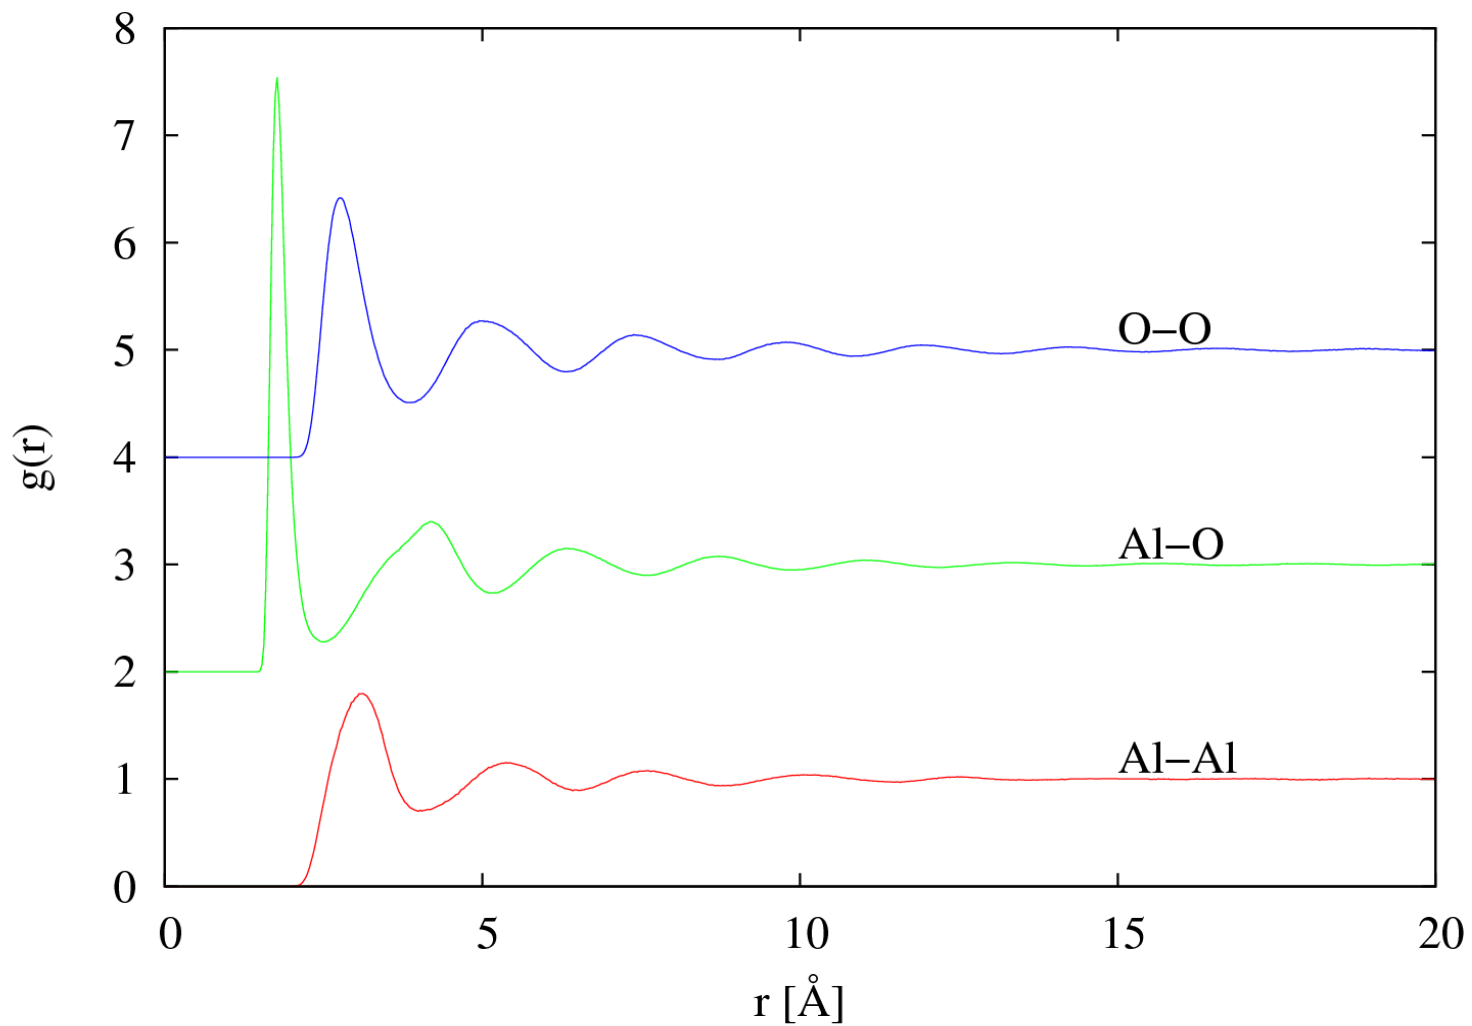

*The problem of tetrahedrally
coordinated glasses and liquids*


(water, α -MX₂, α -Si, α -Ge)

Amorphous SiO₂

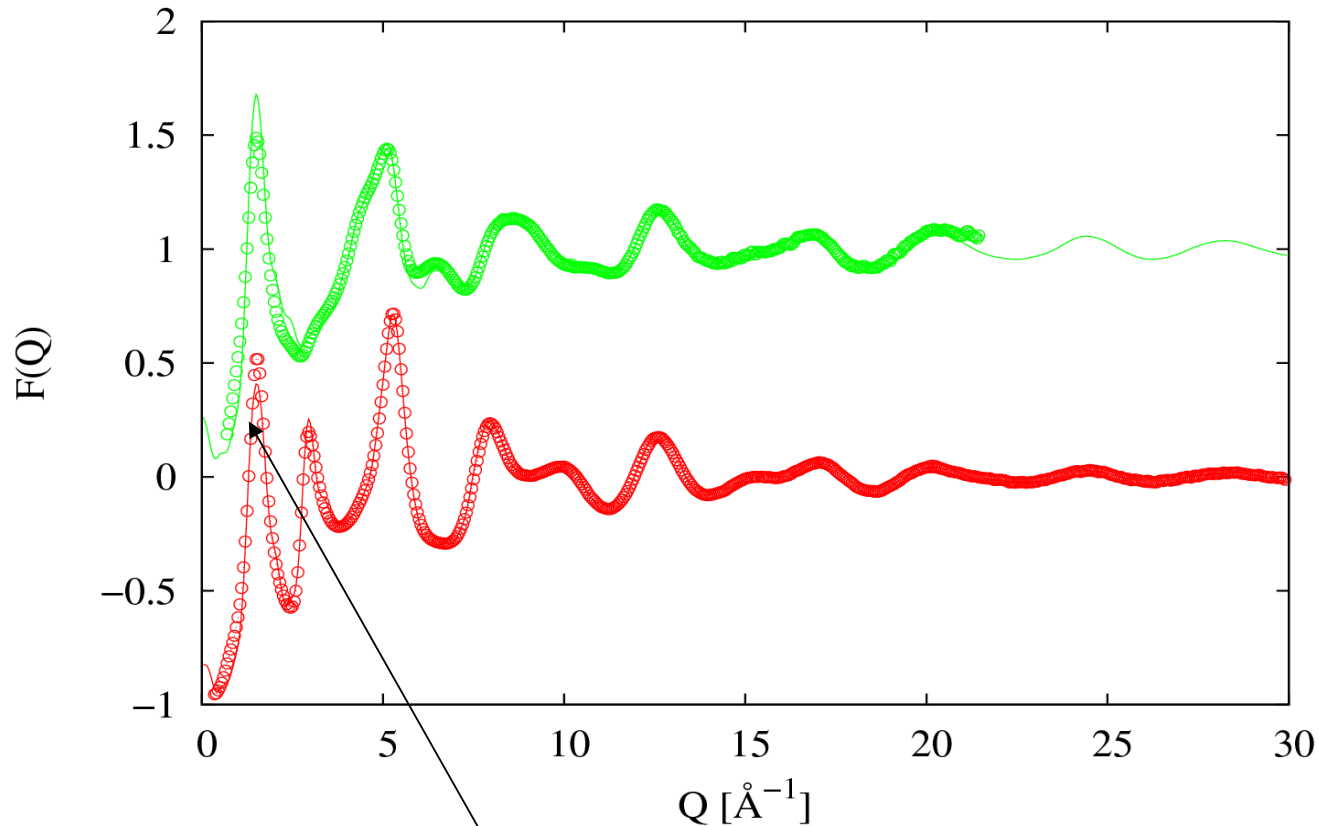


“First sharp diffraction peak” - FSDP


Radial distribution functions:

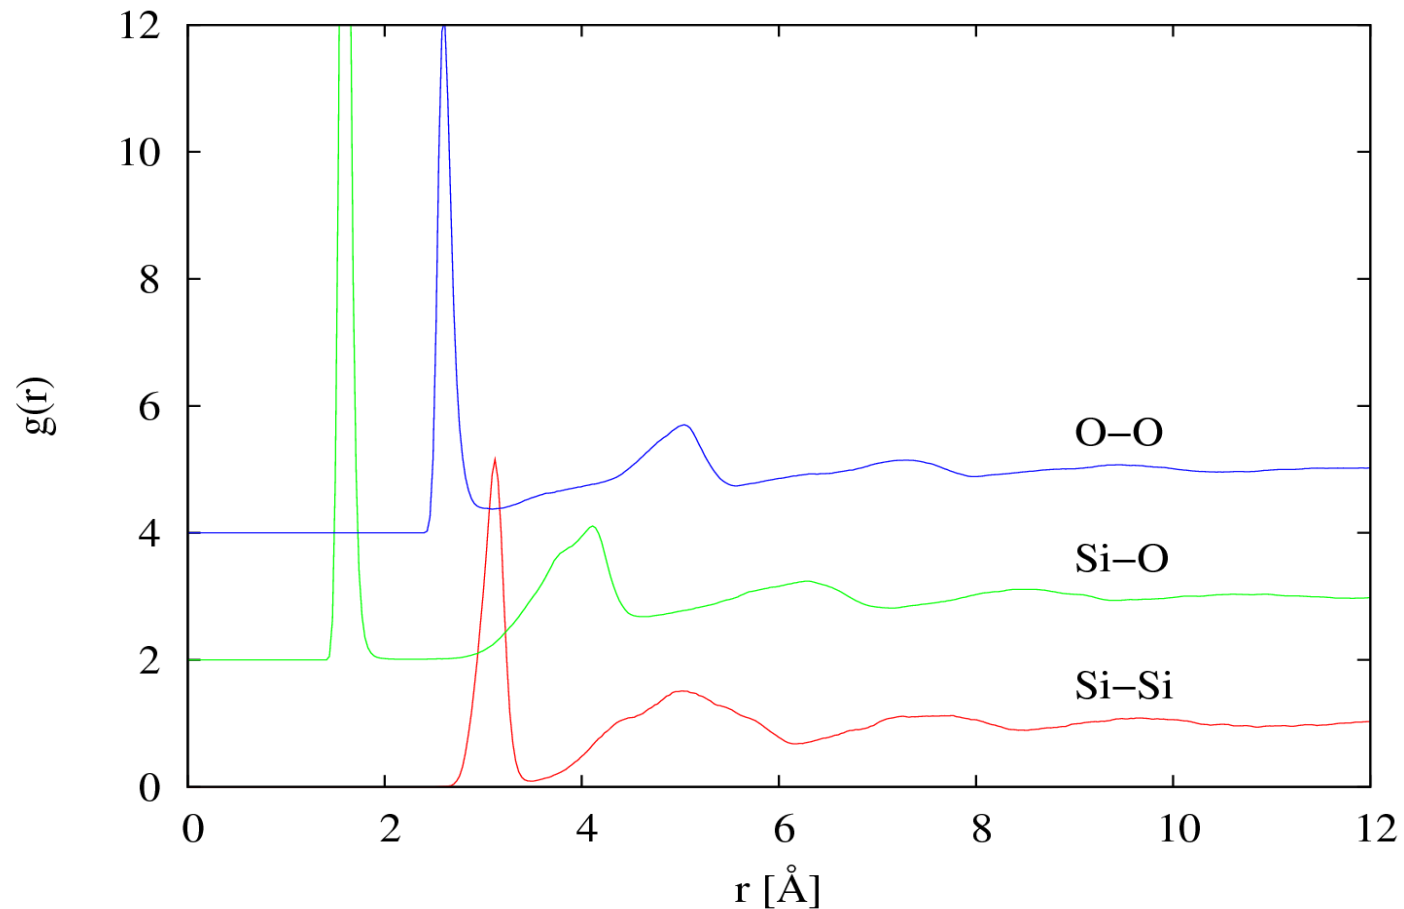


Coordination numbers:

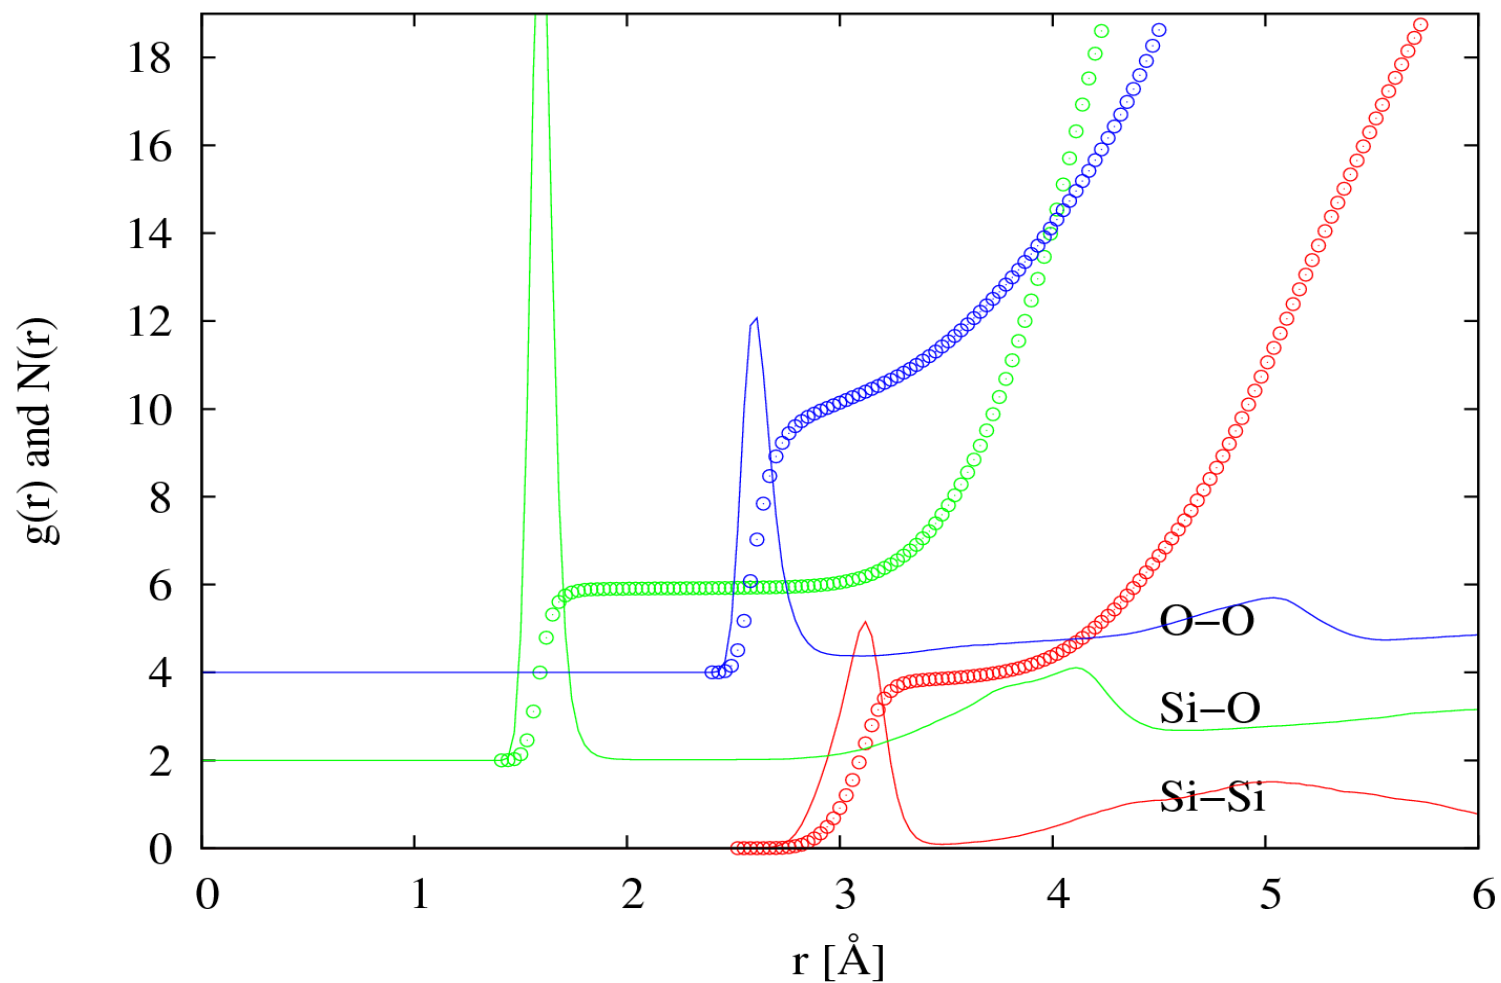


Spatial density function for α -SiO₂:

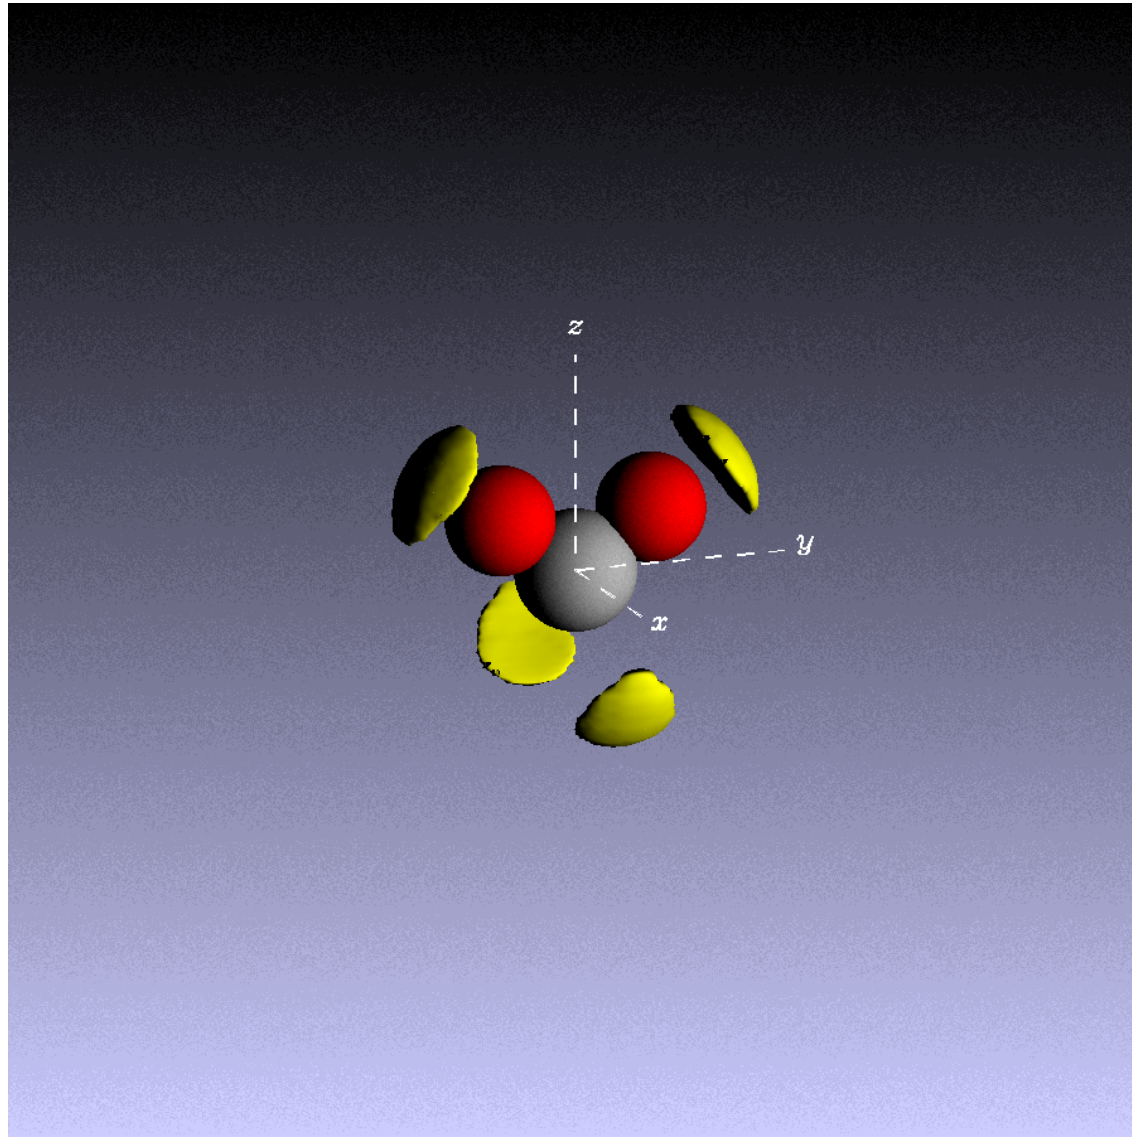


Spatial density function for α -SiO₂:

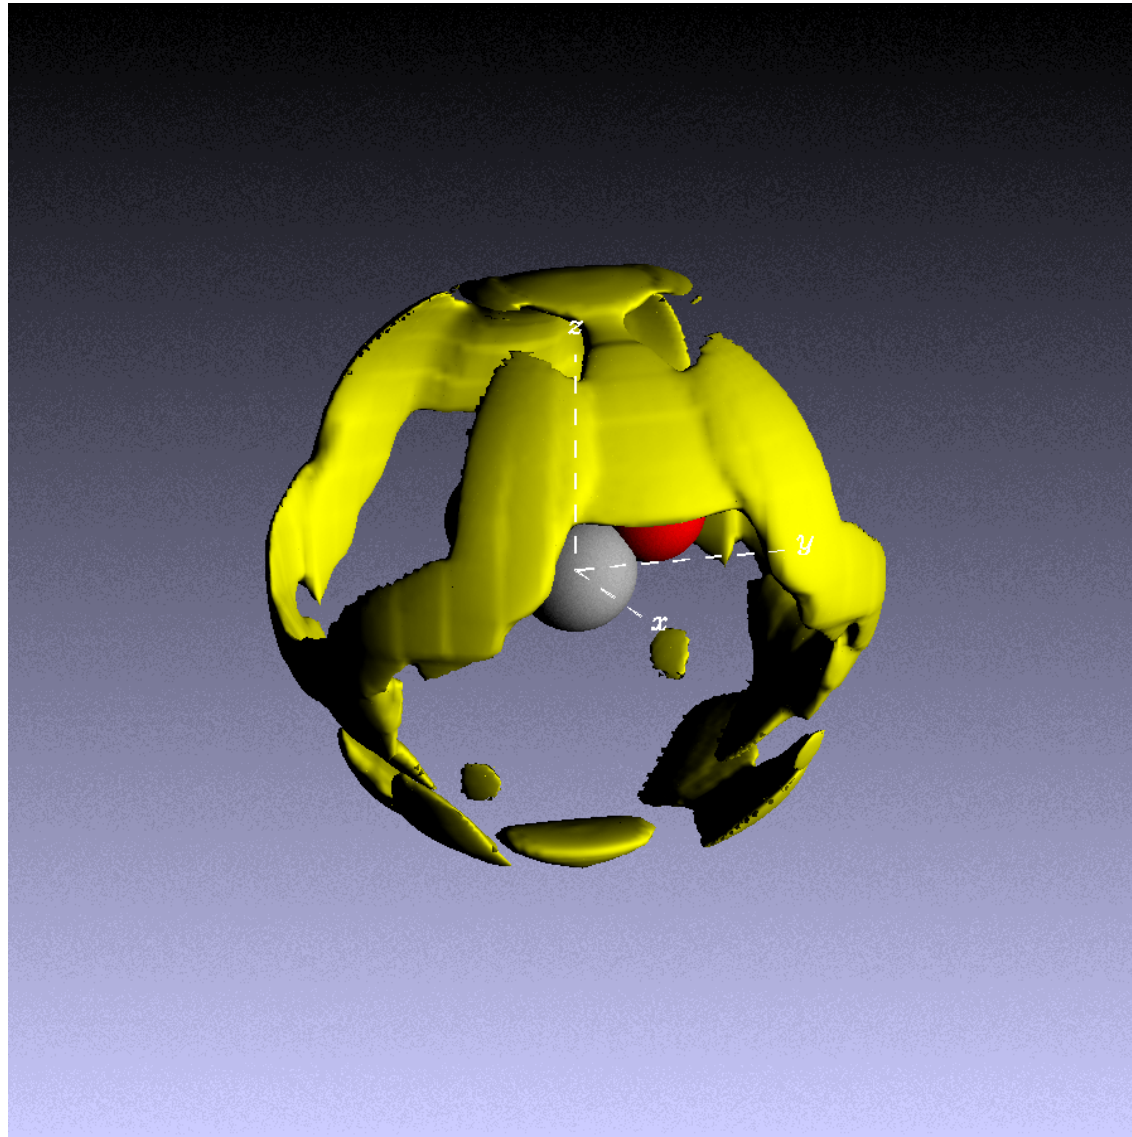

Spatial density function for α -SiO₂:

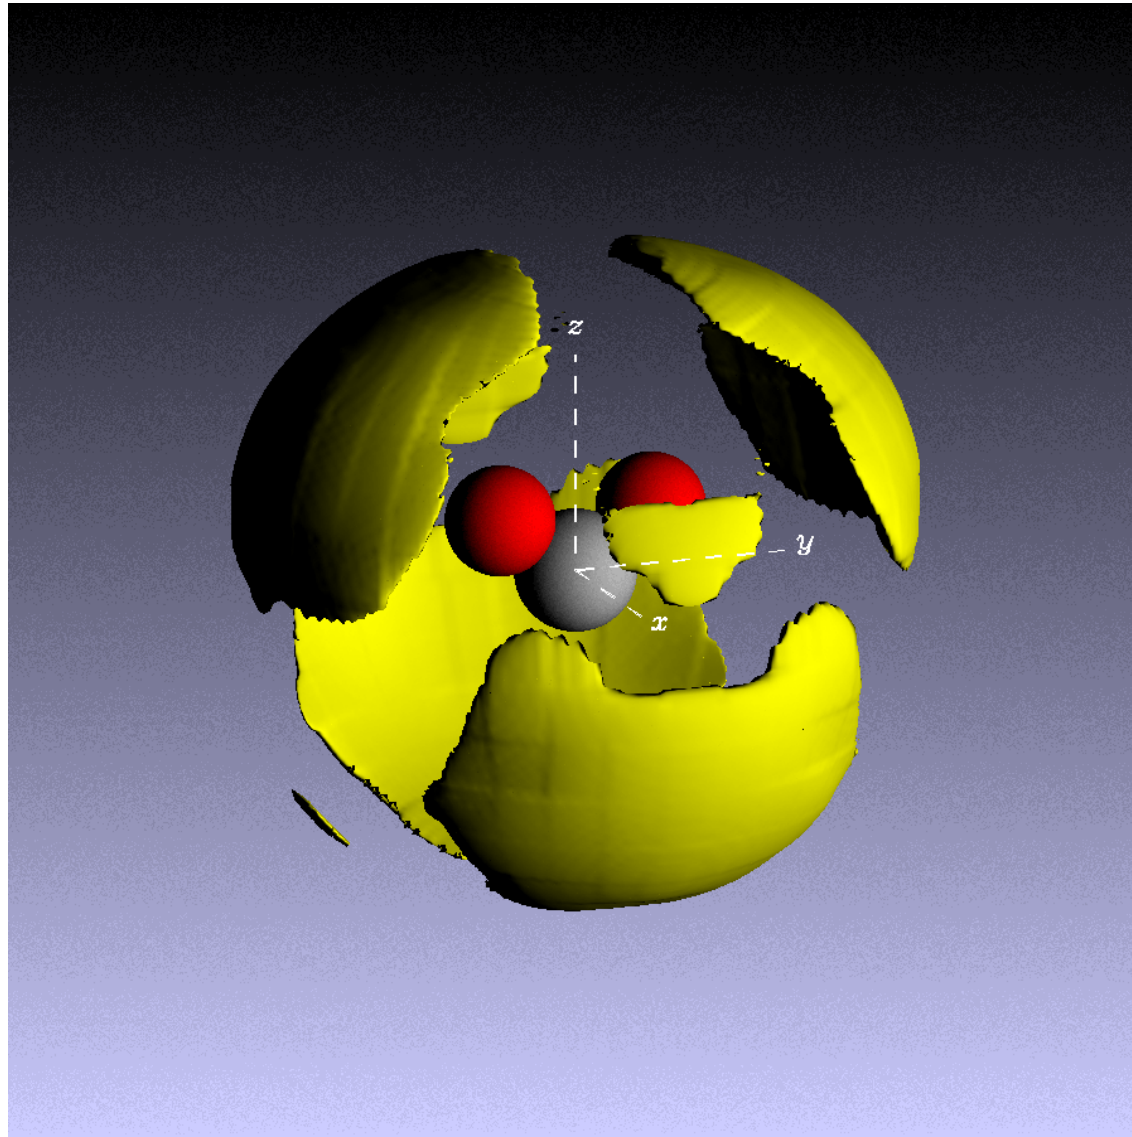


Compare with amorphous Si

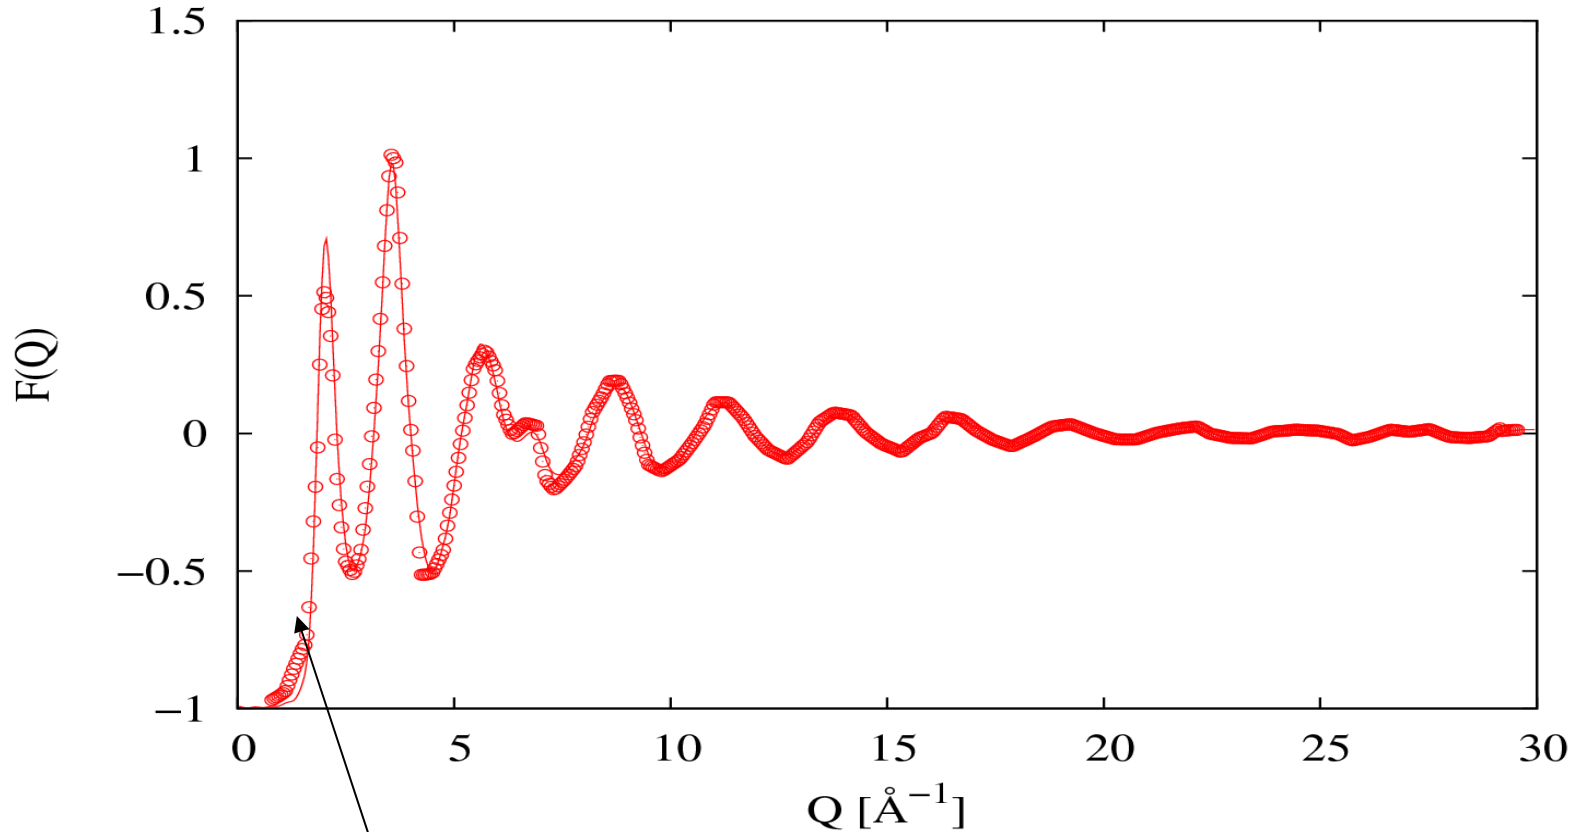


FSDP is absent!

Amorphous SiO₂

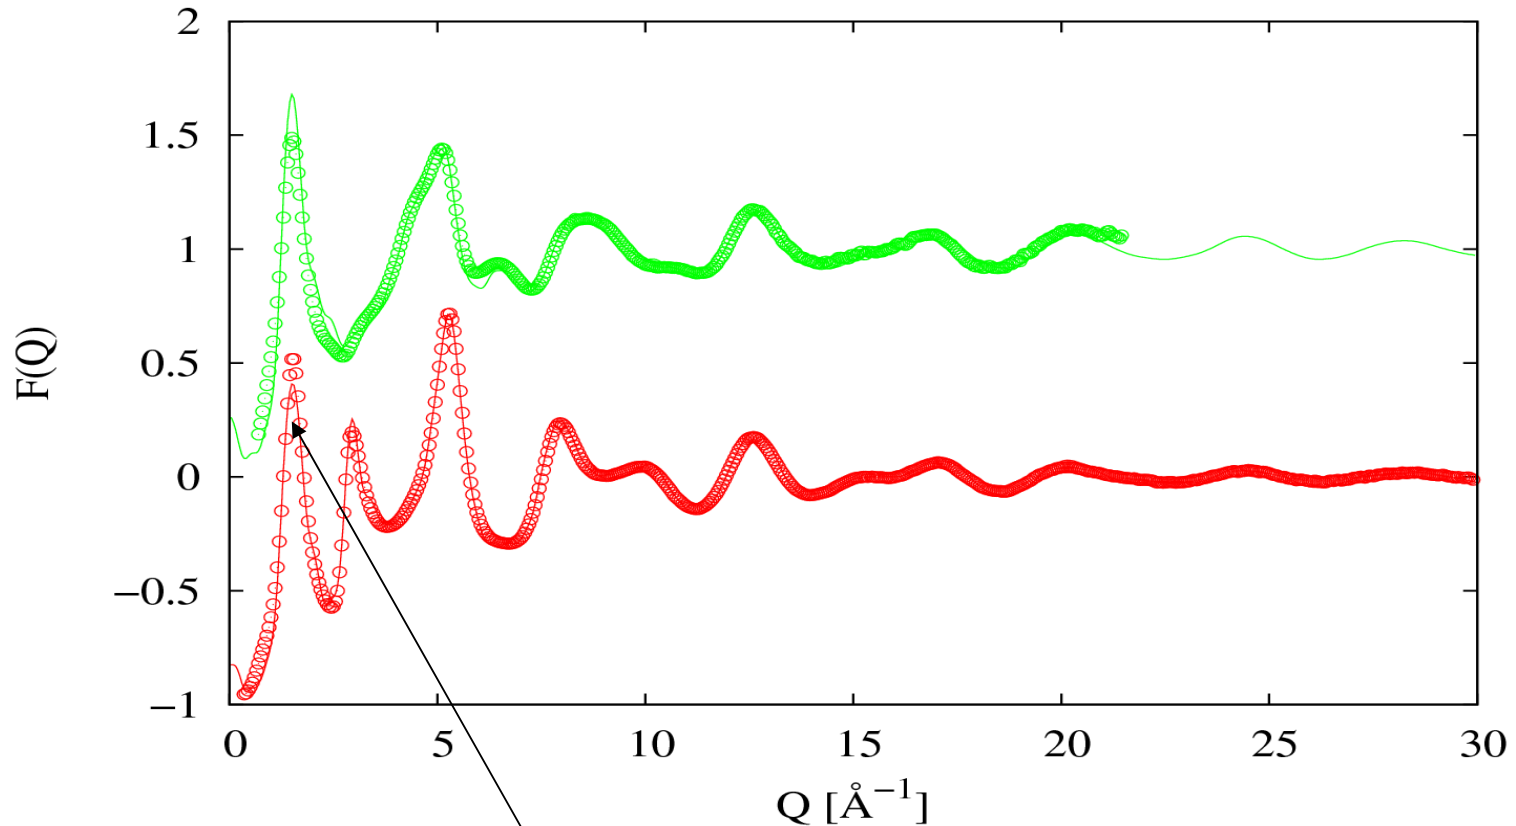


“First sharp diffraction peak” - FSDP



Coordination number- a-Si:

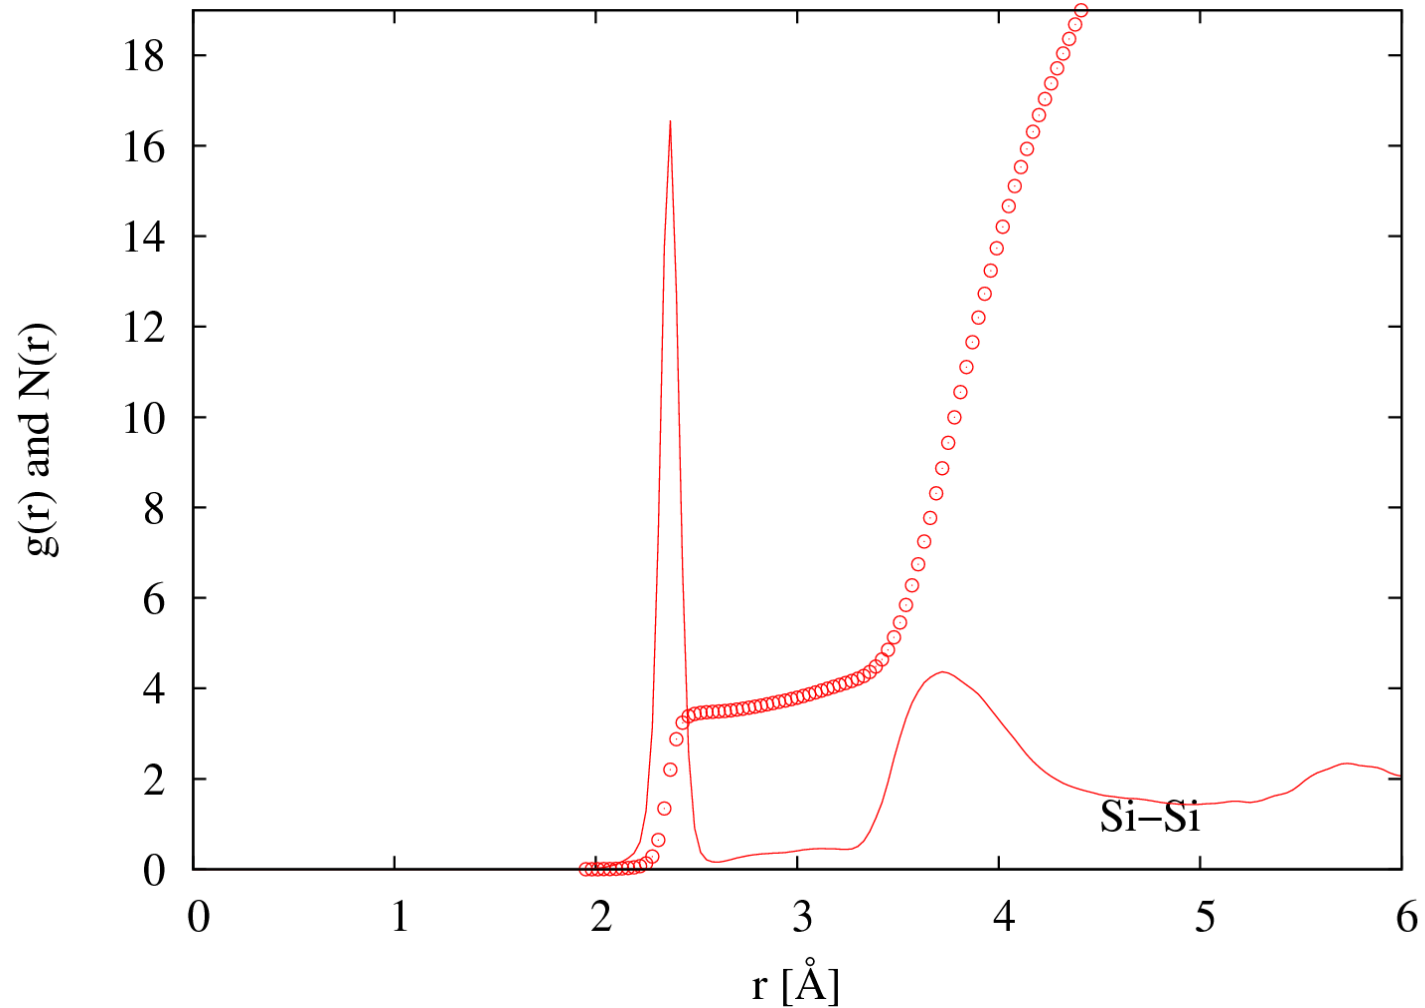



Coordination numbers – α -SiO₂:

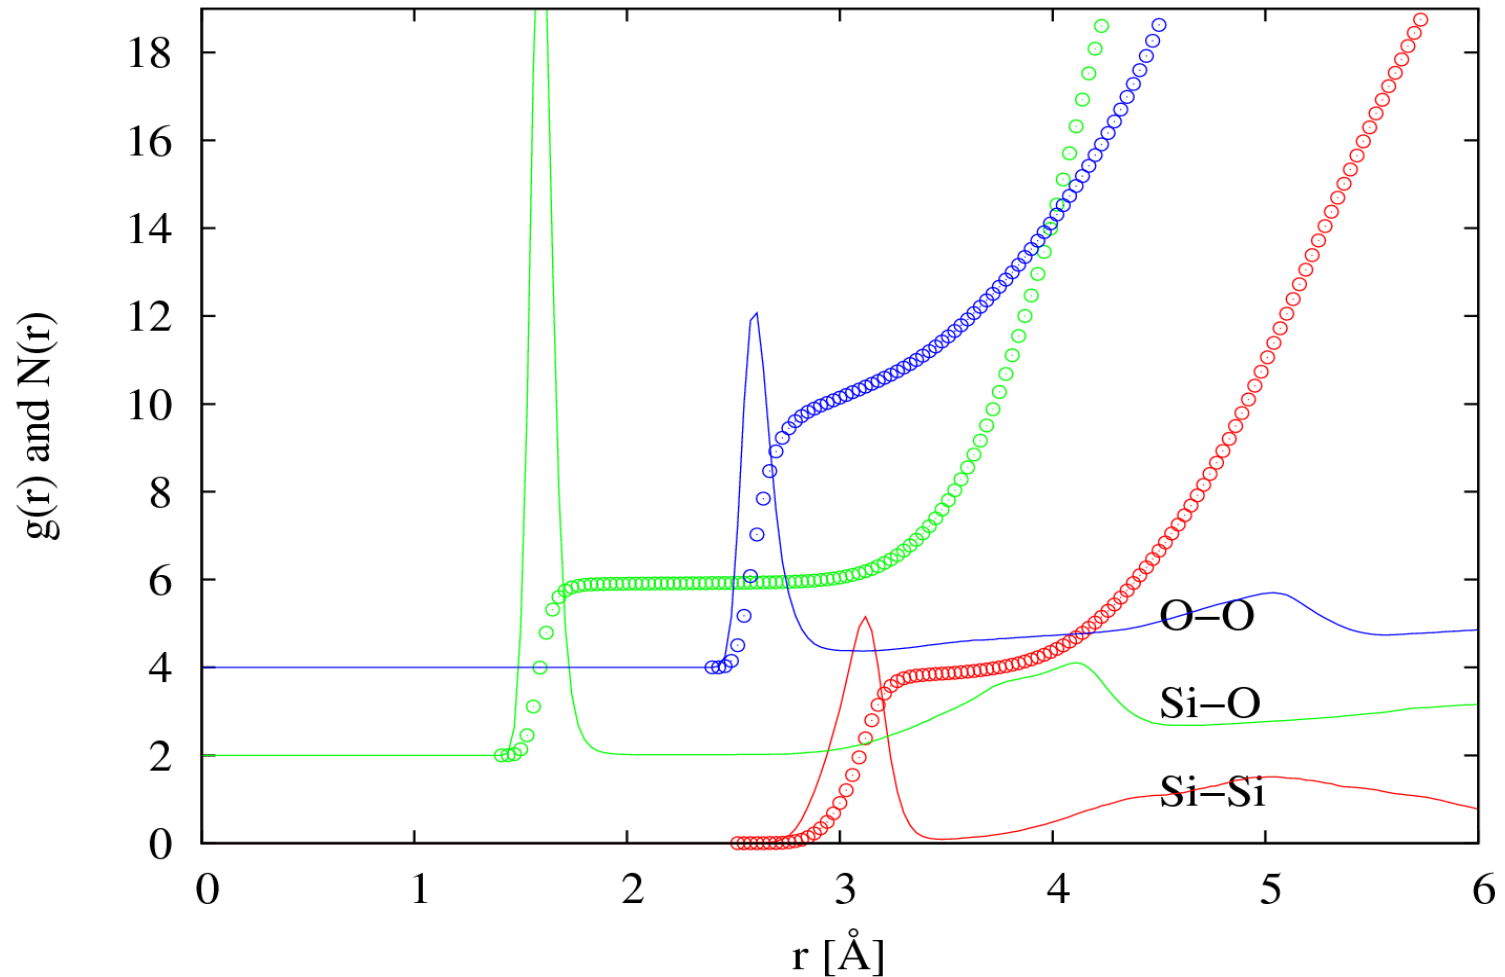

Triangle or “bond angle” distributions, α -Si:

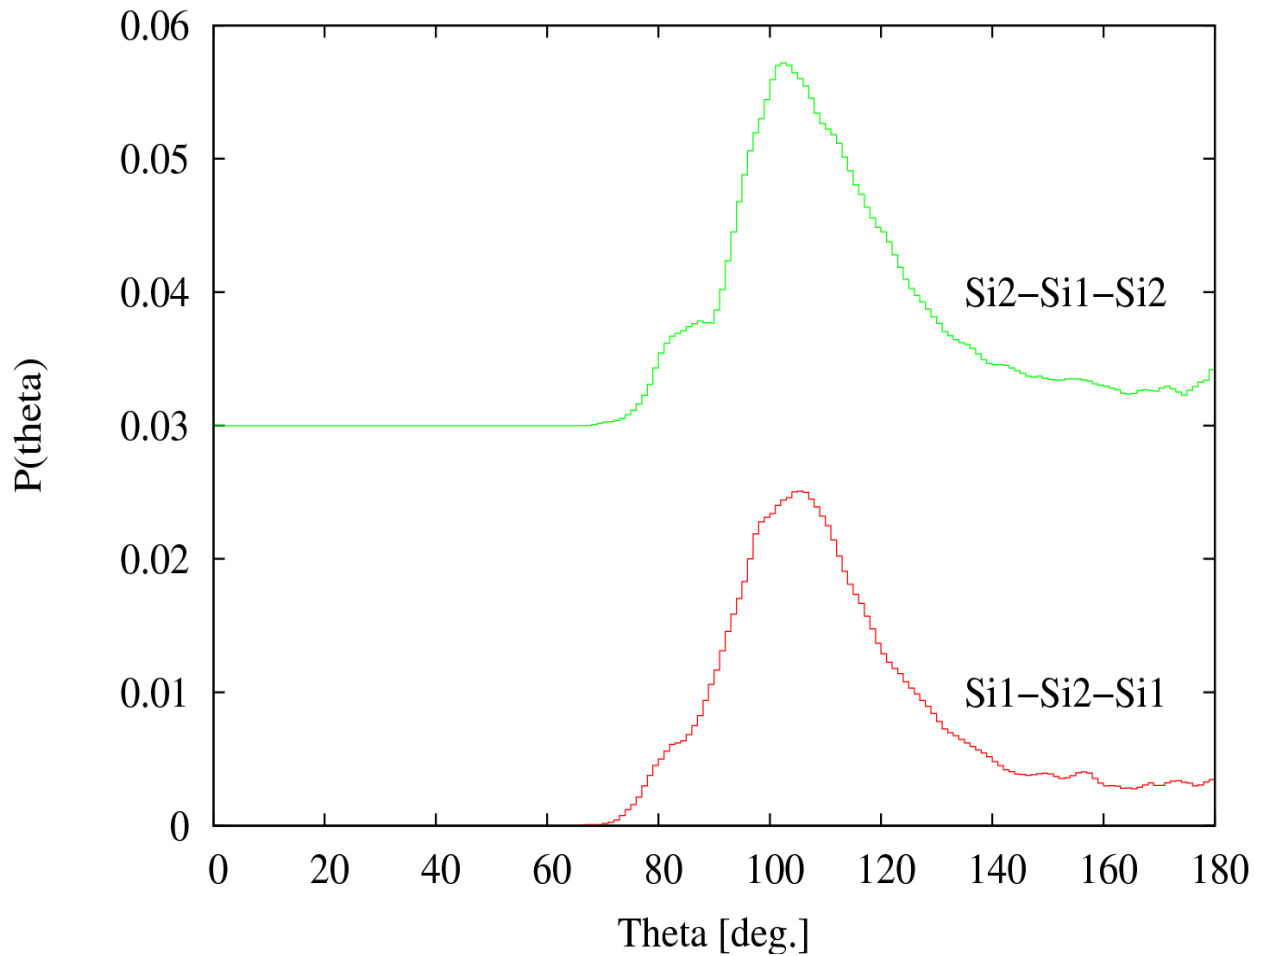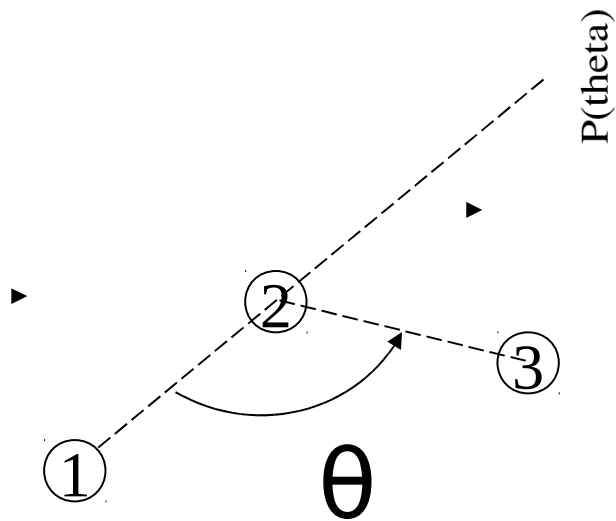

Triangle or “bond angle” distributions, α -SiO₂:

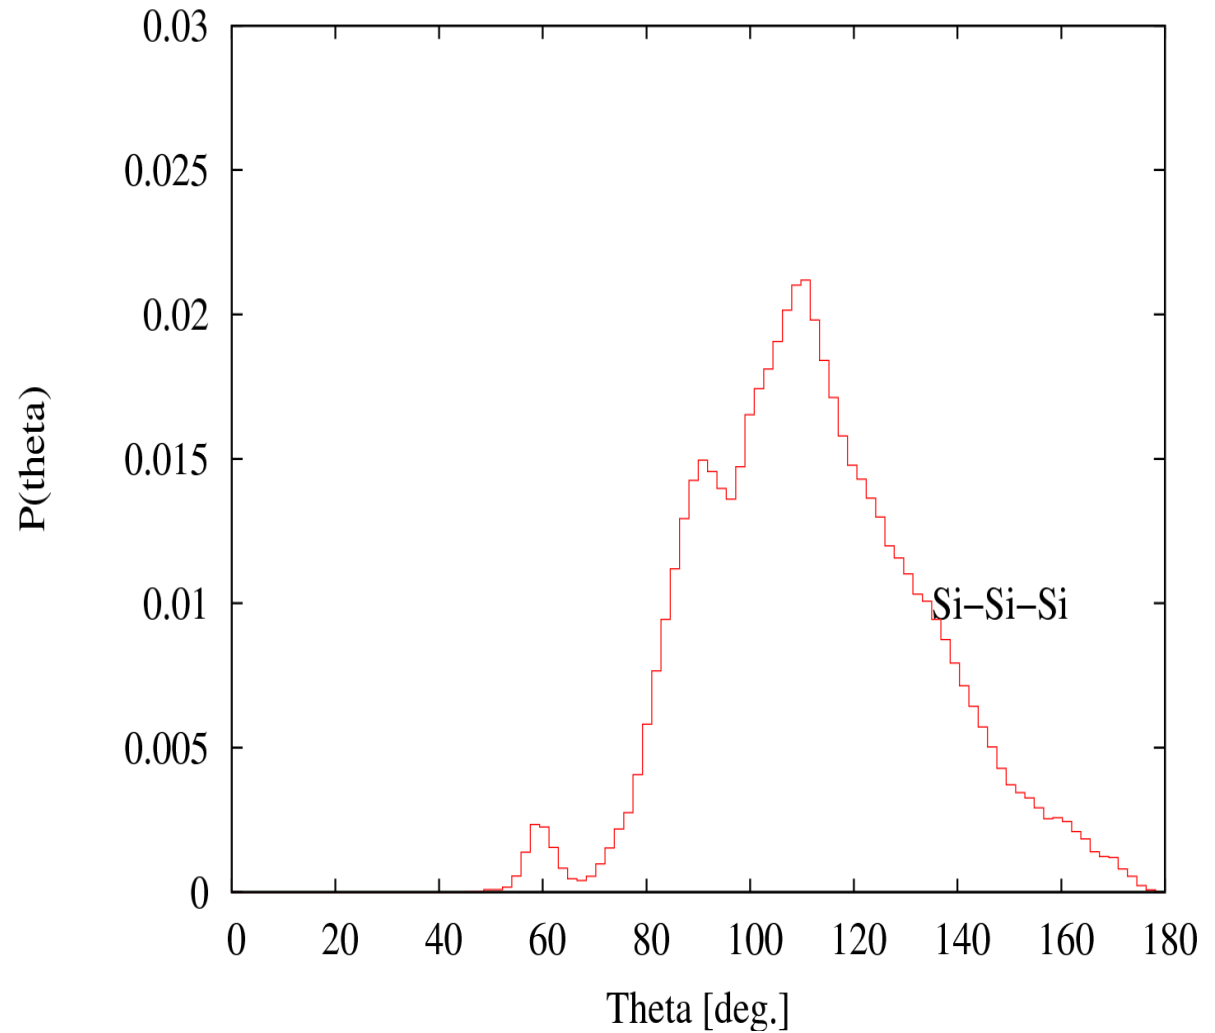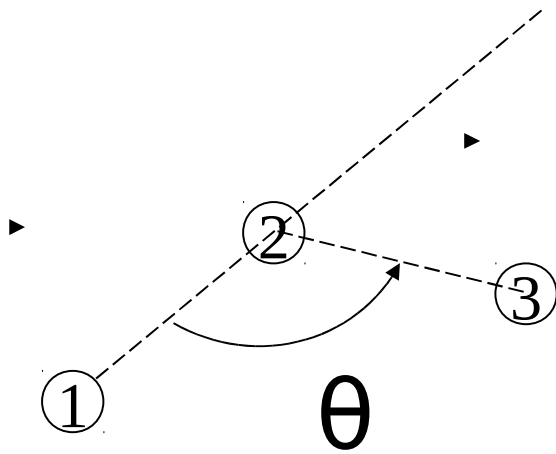

Compare number densities

Renormalise ρ to (near-neighbour distance)³

$$\rho^* = \rho d^3$$

Water: $\rho^* = 0.733$ CN ~ 4.5


a-SiO₂: $\rho^* = 0.685$ CN ~ 4.0

a-Si: $\rho^* = 0.540$ CN ~ 3.8


(*l*-Ni: $\rho^* = 1.270$ CN ~ 12.5)

Compare structure factors...

(renormalise Q to near-neighbour distance)

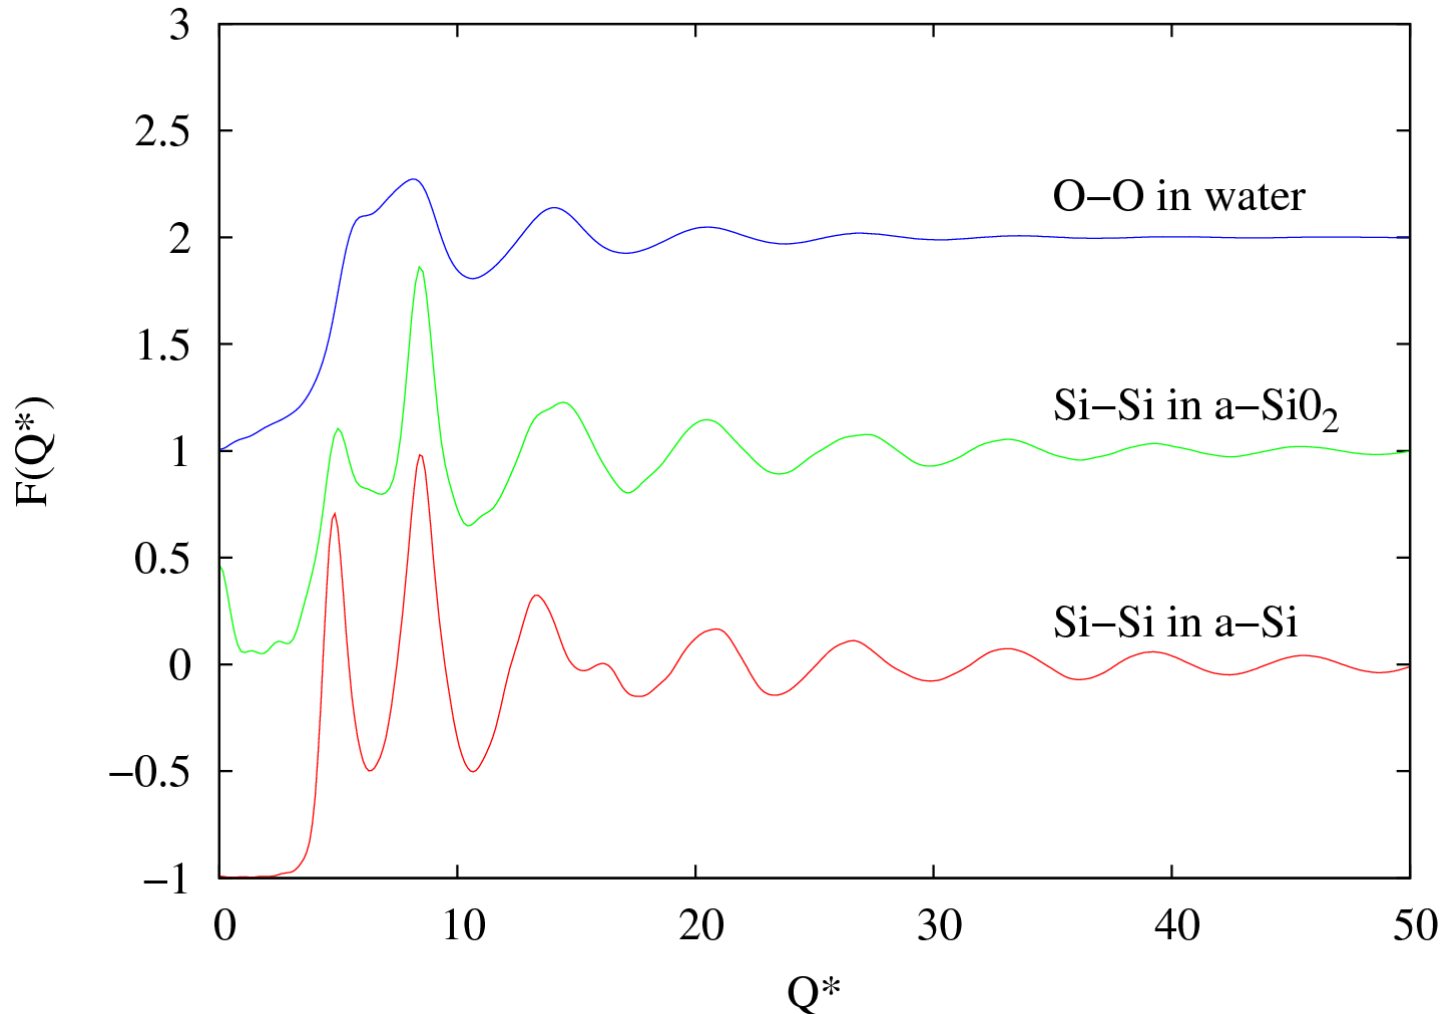

A puzzle: α -(red)P

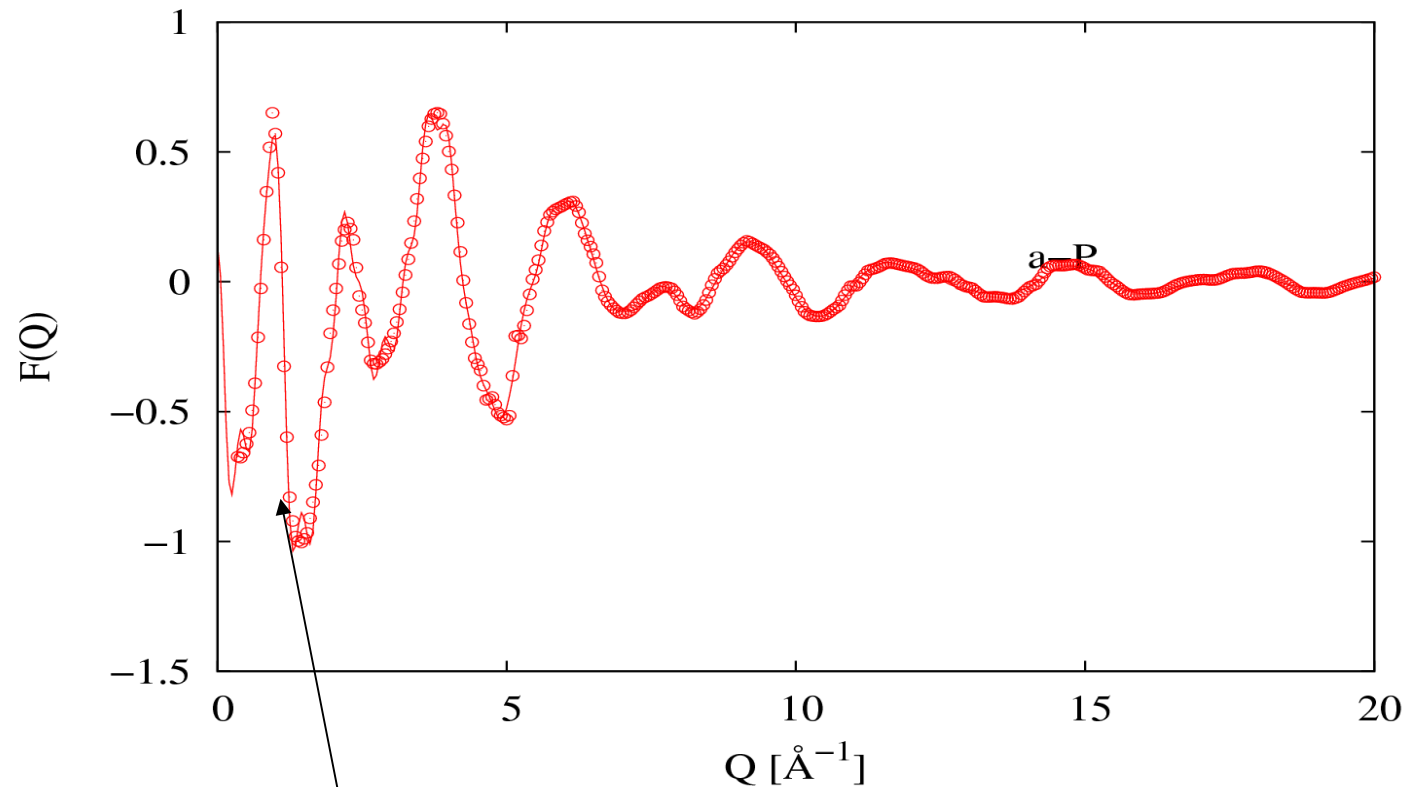

FSDP is present!

Summary (1)

- Disorder is intrinsic to our existence, and occurs over a very wide range of length scales.
- We quantify disorder at the molecular level via the pair correlation function. For molecules this is the *orientational* PCF, which contains more information than the radial distribution functions, $g(r)$.
- Structure factors measured in diffraction experiments are derived from the site-site radial distribution functions.

Summary (2)

- Computer simulation is used to generate a model of the scattering system.
- Diffraction data are introduced either
 - via χ^2 (RMC),or
 - via an empirical potential, (EPSR).
- Simulated ensembles are used to calculate a number of distribution functions not accessible directly from the experiment.

Summary (3)

- Tetrahedrally bonded glasses and liquids show structural similarities.
- Relevance/role of the “FSDP” is unclear.
- We can only really study these properties by forming structural models consistent with the data.

Thank you for your attention!